

Double Networks Of Liquid Crystalline Elastomers With Enhanced Mechanical Strength

Xueyan Lin,[†] Weike Zou,^{‡,†} and Eugene M. Terentjev^{*,†}

[†]*Cavendish Laboratory, University of Cambridge, JJ Thomson Avenue, Cambridge CB3
0HE, U.K.*

[‡]*State Key Laboratory of Chemical Engineering, Zhejiang University, Hangzhou 310027, P.
R. China*

E-mail: emt1000@cam.ac.uk

Abstract

Liquid crystalline elastomers (LCEs) are frequently used in soft actuator development. However, applications are limited because LCEs are prone to mechanical failure when subjected to heavy loads and high temperatures during the working cycle. Mechanically tough LCE system offers larger work capacity and lower failure rate for the actuators. Here we adopt the double network strategy, starting with a siloxane-based exchangeable LCE and developing a series of double-network liquid crystalline elastomers (DN-LCEs) that are mechanically tougher than the initial elastomer. We incorporate polyacrylate reacting monomers to fabricate a DN-LCE, some of which have the breaking stress of 40MPa. We incorporate thermoplastic polyurethane to fabricate a DN-LCE, achieving an enormous ductility with of 90 MJ/m³. We have also attempted to utilise the aza-Michael chemistry to make DN-LCE that retains high plasticity due to several bond-exchange mechanisms, however, it failed to produce a stable reprocessable LCE system using conventional ester-based reactive mesogens. Each of these DN-LCEs exhibits unique features and characteristics, which are compared and discussed.

Introduction

Liquid crystalline elastomers (LCEs) are a unique class of soft materials that incorporate mobile liquid crystalline ordering with rubber-elastic solids. The balance between the two effects enables LCEs to achieve large, reversible length change on the macroscopic scale, when their underlying order parameters change.¹ Due to their increasingly easy fabrication methods, in recent years, a growing variety of LCEs designs were made for the demonstration as mechanical actuators.²⁻⁷ When LCEs are heated, the order parameter decreases and aligned LCEs would contract along with their global mesogen orientation. In this way, LCE actuators convert the energy stored in their phase ordering into mechanical work against the attached load. Because of its simple execution, the thermal stimulus is the most common method to actuate contemporary LCEs.^{8,9} However, thermal actuation imposes a salient problem to LCE's performance as actuators in a practical setting: the elastic modulus of LCEs always decreases as the surrounding temperature increases. This effect becomes more pronounced near the nematic-isotropic transition point when a sudden dip of elastic modulus is observed, often to values much lower than 1MPa before raising again to the isotropic rubber plateau.¹⁰⁻¹² Such a softening dip makes LCEs particular vulnerable to heavy load at high temperatures when the work output is observed decreasing and samples could fail as the consequence.¹³ Therefore, it is a serious problem that obstructs LCEs to becomes a practically useful high-stroke actuator operating through continuous heating cycles, compared to other types of actuators.¹⁴⁻¹⁶

To withstand heavy loads and fully exploit the LCEs actuation potential, a new strategy to toughen LCE without losing their actuation capability is needed. In the past, toughening LCEs at ambient temperature has mostly been attempted by introducing additional physical crosslinking, such as additional crystallinity or hydrogen bonding.^{11,17-21} However, at high temperatures these effects are greatly diminished because crystallites melt away and the hydrogen bonding depletes. As a result, these LCEs does not show sufficient toughness at the height of thermal cycles. Furthermore, because the formation of crystallites in LCEs

often requires minutes at ambient temperature, the crystallinity method can only be used when repeated thermal actuation is not demanded. As for hydrogen bonding, evidence suggests that too much of the hydrogen bonding often conflicts with mesogen interaction and can result in the disruption of alignment, leading to a loss of actuation reversibility.^{22,23}

In this paper, we use the strategy of double networks that offers an alternative solution to the toughening of LCEs. This strategy has been successfully demonstrated in regular hydrogels and elastomers to increase their elastic moduli, breaking stresses and strain-at-breaks, hence the overall toughness.²⁴⁻²⁶ Generally, the double network is constructed by incorporating a rigid network into a soft base network. The rigid secondary network could be sacrificial during excessive loading, and the additional mechanical energy can be dissipated, resulting in much higher stress to break the sample. The base elastic network serves a different role in preventing the crack propagation and preserving the sample integrity even after the local partial breakdown of the secondary rigid network, so the strain-at-break does not significantly decrease. Consequently, the toughness of the double network increases. In practice, the classical way to fabricate double networks is sequential fabrication where the monomers of the rigid networks are introduced into the base network by absorption, and later polymerise *in-situ*.²⁷ After the formation of double networks, the strength and toughness of the base component are greatly enhanced. Unlike the physical bondings, the properties of double networks are less affected by temperature fluctuation due to the stability of covalent bonds in both networks. To date, the majority of double network research focuses heavily on hydrogels, with only a handful of research groups applying this fabrication method to liquid crystalline polymer systems to introduce shape-memory functionality as well as enhanced pliancy.²⁹⁻³¹ Unfortunately, no toughening effect was reported because this strategy only works after a careful design of the ratio between each of the two networks.²⁷ A recent paper described a new method of one-pot synthesis of a double network LCE (DN-LCE) using polyacrylate LCN within a polyurethane LCE.³² Their results show a DN-LCE with a remarkable 50MPa breaking stress measured at room temperature, and 8MPa measured

at 140°C. Noted, in line with our earlier argument on hydrogen bonding disrupting mesogen interaction, the polyurethane LCE they used did not achieve a two-way reversible actuation.

For the practical use of LCEs, their ability to be reprocessed and their mesogen orientation to be reprogrammed is an attractive additional proposition, because the LCEs can therefore be recycled and re-manufactured into more complex geometries without losing actuation capability. However, in double network systems the introduction of reprocessibility has been more challenging. Despite that the two networks are entangled with each other, they should not covalently crosslink before and after the reprocessing. Initially, we attempted to construct such an orthogonal system with siloxane/transesterification,^{35,37,41} by using a combination of thiol-ene, aza-Michael and photopolymerisation reactions. However, we later realised that the aza-Michael network is participating in side reactions, which results in fusion of the two networks and a decrease of the mechanical strength. We discuss this type of material to highlight its properties, since using aza-Michael reaction has been one of the common ways to fabricate LCEs nowadays.^{19,21,45}

Here we report the fabrication of three different types of DN-LCEs and discuss the effects of the different additional networks on their final properties. Firstly, in all cases, a soft xLCE is used as the base network, which contains siloxane-exchange functionality for network reconfiguration. Using different fabrication methods, this base xLCE is then interpenetrated with three different materials: (1) mesogenic permanent enhancing network, and (2) thermoplastic non-mesogenic network. We also explore (3) an ‘unsuccessful’ double network obtained using aza-Michael chemistry. We use the classical method of immersion, where the monomers are diffused into the pre-made base network before they are radically crosslinked into the enhancing networks. We also explore a one-pot fabrication method where the thermal plastic polymer is diffused during the fabrication of the base xLCE. We then proceed to investigate the resultant three DN-LCEs and compare them in terms of their mechanical properties, their ability to flow at elevated temperatures, and their capacity for thermal actuation.

Experimental details

Acrylate mesogenic reacting monomer (RM82, 95% purity) was purchased from Daken Chemical Ltd. Thermoplastic polyurethane filament TPU95A was purchased from Ultimaker. Non-mesogenic monomer tri(propylene glycol) diacrylate (diA) and non-mesogenic monomer bisphenol A diglycidyl ether diacrylate (diBP) are used in control experiments. Chain-extender 3-amino-1,2-propanediol (APD, 97% purity), thiol spacer 2,2'-(ethylenedioxy) diethanethiol (EDDT, 95% purity), siloxane spacer 1,3-divinyl tetramethyl disiloxane (DVS, 97% purity), siloxane crosslinker 2,4,6,8-tetramethyl 2,4,6,8-tetravinyl cyclotetrasiloxane (TVCS, 95% purity), thiol-ene catalyst dipropylamine (DPA, 99% purity), siloxane-exchange catalyst 4-(dimethylamino) pyridine (DMAP, 99% purity), photo-initiator Irgacure 651 (I-651, 99% purity), anti-oxidant butylated hydroxytoluene (BHT, 99% purity) were all purchased from Sigma Aldrich and used without purification. We use UV LED purchased from New Energy (365nm, 875mW) for the photo-polymerization.

Synthesis of the single network Si-SN and Aza-SN

A number of single networks were used in this study, and their structures are shown in Fig.1. There were in total six single networks, and they are divided into mesogenic or isotropic categories. Siloxane exchange and transesterification are the two bond-exchange reactions used for making reprocessable DN-LCE, and their enabling functional groups are highlighted in the schemes in Fig.1. In order to fabricate DN-LCEs, Si-SN was used as the fixed base network, combined with different types of enhancing secondary networks (except on one occasion the Si-SN was replaced by the non-mesogenic counterpart diBP-SN for a control experiment). We now describe the steps to prepare stand-alone Si-SN and Aza-SN, because its rest of the single networks are made only during the fabrication of DN-LCEs, which will be discussed later.

Si-SN: Si-SN is made by following a procedure used in making siloxane-based xLCE.⁴¹

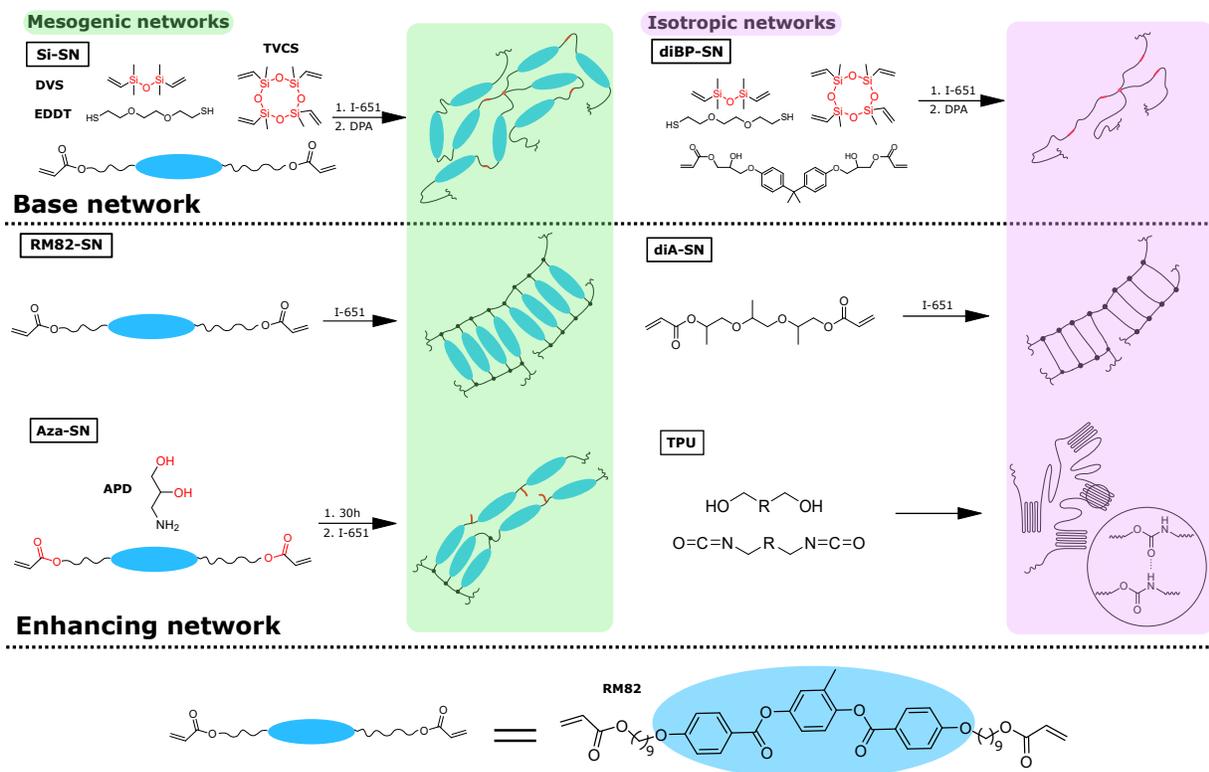


Figure 1: Reaction schemes of each type of single network. These single networks are divided into mesogenic and isotropic, as indicated by green and purple shade. Si-SN is used as the base network and it is combined with the four types of secondary ‘enhancing’ networks (RM82, Aza, diA, and TPU) into DN-LCEs. On one occasion, diBP-SN was used to replace Si-SN for a control experiment. The functional groups, which are responsible for siloxane exchange and transesterification, are highlighted in the schemes.

3.38g RM82, 1.26g EDDT, 0.188g DVS and 0.156g TVCS are used to make multiple Si-SN samples at once in one batch. The synthesis of Si-SN includes two steps: firstly load EDDT, DVS and TVCS in a vial along with 10mg(1wt%) I-651. No solvent is added at this step. Stir the liquid mixture while exposing it to 365nm UV light for 5 minutes to produce the thiol-terminated oligomer. The resultant viscous oligomer is then combined with RM82 (dissolved in 3g toluene), 20mg(2wt%) DPA and 10mg(1wt%) DMAP (dissolved in a minimal amount of acetonitrile), which is the siloxane-exchange catalyst. Degas the mixture in a vacuum, pour the solution into a homemade PTFE dogbone mould designed for optimal mechanical testing, and cure in a hot press at 60°C. The samples are then peeled off from the mould and dried in a vacuum overnight.

Initially, dimethylformamide (DMF) was used as the solvent for the synthesis of Si-SN, in order to facilitate the thiol-acrylate reaction speed. However, we found that DMF can react with siloxane-based crosslinker DVCS, so the resultant Si-SN had a lower gel fraction: gel fraction of Si-SN is 78% when using pure DMF as the solvent, but it rises to 85% when using toluene : DMF= 1 : 1, and to 94% when using pure toluene. Henceforward, we fabricated all Si-SN in toluene. It may appear sensible by replacing exchangeable DVCS with a permanent vinyl-based crosslinker, such as (1,3,5-triallyl-1,3,5-triazine-2,4,6(1H,3H,5H)-trione, as it would provide more stability during the fabrication process. But this eliminates the possibility for the base network to flow at high temperatures, which is essential to allow the base network to adapt to the deforming secondary network during alignment.

Aza-SN: 812mg RM82 and 100mg APD are used to make this type of single network through the aza-Michael reaction, with acrylate groups in 10% excess.¹³ Over time, acrylate slowly reacts with the primary amine of APD and generates the acrylate-terminated liquid crystalline linear polymer, which is then crosslinked under UV by acrylate photopolymerization. Firstly, mix both reagents with 5mg(0.5wt%) BHT, 10mg(1wt%) DMAP, and 360mg DMF in a vial. Seal the vial with the nitrogen atmosphere and place it at 90°C for the next 30 hours. The brown-yellow viscous resin containing liquid crystalline polymer

is diluted with an extra 2g DMF, and 20mg I-651 is added in. Degas the resin in vacuum, before pouring it into a PTFE dogbone mould and cured under 365nm UV. The samples are then collected from the mould and dried in a vacuum overnight.

Synthesis of DN-LCEs

In order to make double networks, Si-SN is used as the base network. Four DN-LCEs were fabricated in this way, with two of them having mesogenic secondary network, and two having isotropic secondary networks. These four DN-LCEs, along with an additional one made using the non-mesogenic diBP-SN, are listed in Table.1 For example, Si-RM82 is made by combining the base Si-SN with mesogenic RM82-SN, according to the table, and it is made by the immersion method. The three resulting DN-LCEs that we mainly focus on in this paper are highlighted in the Table 1, while the remaining two DN-LCEs were used for control experiments.

Table 1: Table of DN-LCEs used in this work. Each of their constituent single networks, their fabrication methods, their ability to plastically flow, and their ability to actuate is listed in respective columns.

DN-LCEs	Base SN	Enhancing SN	Fabrication methods	Flow at high T	Actuation
Si-RM82	Si-SN	RM82-SN	Immersion	X	✓
Si-Aza	Si-SN	Aza-SN	Immersion	✓	✓
Si-diA	Si-SN	diA-SN	Immersion	X	X
Si-TPU	Si-SN	TPU	One-pot	✓	✓
diBP-TPU	diBP-SN	TPU	One-pot	✓	X

Si-RM82: 0.6g RM82, 30mg (2wt%) I-651 are dissolved in 2.4g toluene under mild heating, making up a clear solution of 20wt% RM82 concentration. Si-SN dogbone samples synthesised previously are submerged into the solution and allowed to be fully swollen at 60°C for the next 3 hours. The swollen gels are then dried in vacuum to afford the pre-cured Si-RM82 that still contains the absorbed, uncrosslinked RM82 monomers inside. The samples taken out from the oven can be photo-polymerised in room temperature into (a) polydomain DN-LCE in a load-free state; or (b) aligned monodomain after 200% strain is maintain

during UV exposure. For the synthesis of Si-diA, Si-SN is similarly swollen into a 20wt% non-mesogenic diA solution in toluene then dried in a vacuum oven and photo-crosslinked afterwards. After extensive testing, 20wt% solution was our optimal RM82 concentration in the making of Si-RM82, because the resultant Si-RM82 sample was able to show greater toughness without losing its ability to thermally actuate. The percentage weight increase of Si-SN after monomer absorption is shown in Tab.2. The absorbed monomers in this process is 35wt% to the base Si-SN mass.

Table 2: The percentage weight increase of Si-SN after immersing in different RM82 toluene solutions for 3h at 60°C, and dried. From a range of tested solutions, we used 20wt% solution in the rest of this work, as it affords Si-RM82 with optimal toughness/actuation combination.

RM82 concentration in solution (wt%)	5	10	20	30
Weight increase compared to Si-SN (%)	4	22	35	46

To verify the complete independent formation of the two networks in Si-RM82, an ATR-FTIR test was conducted before and after the Si-SN being swollen in RM82 solution, as well as after the polymerisation under UV, see Fig.2.

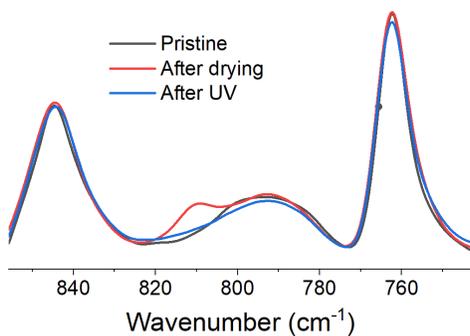


Figure 2: The ATR-FTIR shows the acrylate peak (812 cm⁻¹) appears after the Si-SN absorbing RM82 monomers from solution. This peak subsequently disappears after UV exposure.

Si-TPU: The amount of TPU polymer added into the network is 50wt% of the Si-SN amount. Mix 5mg I-651, 252mg EDDT, 38mg DVS and 31mg TVCS in a vial without addition of solvent. Place the vial under UV and photo-polymerise EDDT with DVS and

TVCS, same as previously described in the synthesis of Si-SN. In a separate vial add in 500mg thermoplastic TPU95A and 672mg RM82 and dissolve them with 5g DMF at 60°C. When the TPU95A and RM82 fully dissolve, mix the two vials together and add in 50mg amount of DPA. Pour the solution into a PTFE mould and leave the mould at room temperature until gelation, before evaporating the solvent at 60°C overnight. For the control isotropic DN-LCE diBP-TPU, repeat the same procedure, but replace the RM82 with an equal molar amount of non-mesogenic monomer diBP.

Si-Aza: prepare 0.5g RM82, 61mg APD 5mg (1wt%) DMAP and 10mg (2wt%) I-651. Add in 2.3g 10:1 toluene/acetonitrile solvent and dissolve all the reagents at 60°C. A small amount of acetonitrile is added here to help APD dissolve without precipitating RM82 out. Then, the base Si-SN dogbone samples are added into the vial to swell at 60°C. The vial is left in the oven for the next 30 hours. Take out the dogbone samples after the reaction and clean their surface from the residual liquid crystalline resin, before drying them on a PTFE substrate in a vacuum. The weight increase of Si-SN after this process was 31wt%, representing the total amount of monomers absorbed. The dried dogbones, are then cured under a 365nm UV light at room temperature – again, either directly in a polydomain form, or as an aligned monodomain under extension.

Characterisation

The storage and loss moduli of all samples are obtained in TA DMA850, in tensile mode at a fixed 1Hz and a constant temperature ramping rate of 2°C/min. The same instrument is also used for recording stress relaxation enabled by bond-exchange reactions. For stress relaxation tests, samples are first heated up to 230°C, stretched by fixed 1% tensile strain for Si-Aza and Si-TPU samples, and by 0.1% strain for a much more rigid Si-RM82 sample. Recording the stress relaxing over time lets us compare the relaxation curves for different DN-LCEs. Reprocessability test is carried out by cutting the DN-LCE samples and placing them under a 200°C hydraulic press for 1h, in order to observe whether the DN-LCE pieces have fused

together due to bond-exchange reaction or remained separate in a true thermoset. Uniaxial tensile tests of DN-LCEs are carried on a universal testing machine (Tinius Olsen 1ST), at a constant strain rate of 0.01/s, with the breaking stress, strain-at-break of each sample are recorded. Thermal actuation and blocking stress test are again carried in DMA850 in tensile mode. In order to test natural thermal actuation, a very low 50KPa stress is applied to keep the sample taut. Strain (or natural length) change during actuation is recorded when the furnace is cycled between 30-150°C at a ramp rate of 5°C/min. For the thermal actuation at a high load, 1MPa stress is applied instead. Blocking stress is the stress generated inside the elastomer as it is heated up at a fixed strain. In our case, we measure blocking stress when the sample is fixed at a low 0.1% strain (to keep the sample taut) while being heated up from 20°C to 160°C at a rate of 5°C/min. For the iso-stress creep test in Si-TPU system, the sample is first loaded with a constant 0.5MPa stress, and then the furnace is heated up from room temperature to 180°C at a rate of 3°C/min, while the increasing strain (plastic creep) is recorded against temperature. The toughness of all our DN-LCEs is measured by calculating the stored mechanical energy: the area under each of their stress-strain curve until the failure point.

Results and discussion

We begin our discussion with Si-RM82 double network, which combines the exchangeable Si-SN and the permanently crosslinked RM82-SN network. This type of DN-LCE has a high breaking stress and a large elastic modulus. We then proceed to one-pot synthesis of Si-TPU DN-LCE. This type of DN-LCE displays an enormous ductility, with only slightly lower breaking stress compared to Si-RM82. In the end, we explore a combination of Si-SN and Aza-SN. We found this type of DN-LCE is able to relax stress completely by plastic creep at high temperatures. However, it comes at the cost of reduced strength. We also noticed side reactions taking place in Si-Aza at high temperatures, which can result in a

permanent lose of mesogenic power and a reduction in the crosslinking density.

Si-RM82 double network

Si-RM82 samples are made by swelling Si-SN base network in toluene containing mesogenic monomers RM82, with photo-initiator. The pre-cured Si-RM82 is opaque after drying because the base Si-SN is in its polydomain state. When a sufficiently large strain is applied, the pre-cured sample becomes transparent indicating the aligned monodomain state. That is, the presence of RM82 monomer does not affect the alignment of Si-SN. On the contrary, these monomers can be also aligned by mechanical strain due to the template effect of the intact liquid crystalline order inside the Si-SN.⁴⁶ The overall process is therefore analogous to that found in the “Polymer Stabilized Liquid Crystal” (PSLC) scaffold where mesogens are aligned by liquid crystalline polymer filaments nearby.^{47,48} Si-RM82 sample fabricated by UV-curing them in aligned state is found to be permanently fixed in that state. In contrast, if we UV-cure the sample while no strain has been induced, the Si-RM82 fabricated remains opaque and fixed permanently in its polydomain state. Figure 3(a) shows the images of the fabricated opaque polydomain Si-RM82 and the transparent monodomain Si-RM82. The X-ray diffraction confirms that mesogens have been permanently aligned in Si-RM82, Fig.3(b). To demonstrate that the two networks are not chemically linked, fresh Si-SN before and after RM82 absorption, as well as after its UV exposure are characterised in ATR-FTIR. The result is shown in Fig.5(b).

This fixed mesogen alignment during the fabrication of Si-RM82 can dramatically affect their uniaxial tensile behaviour, and the typical results are shown in Fig.3(c). From this graph we notice several features: (1) Without the apparent cost of ductility, the monodomain Si-RM82 has over twice the breaking stress (40MPa) from that of polydomain Si-RM82 (18MPa), owing to the anisotropy of RM82-SN therein. A similar relationship between network anisotropy and tensile strength has been previously reported in double networks hydrogel systems, although to a less pronounced degree.⁴⁹ (2) Both Si-RM82 samples display

a much stiffer tensile response compared to the base soft Si-SN (shown later), which is again attributed to the rigid RM82-SN. (3) Not seen in monodomain Si-RM82, a serrated plateau exists at around 12MPa in all the polydomain system was systematically observed. Such a feature is undoubtedly the consequence of isotropic polyacrylate network being broken down into smaller clusters.⁵⁰ For the same reason, we notice that after this plateau the strain of polydomain Si-RM82 is already very close to sample failure. Such a plateau does not appear in monodomain Si-RM82, which we assume is due to the aligned polyacrylate filaments. In conclusion, crosslinking the pre-cured Si-RM82 in its monodomain state produces Si-RM82 that has a significantly increased breaking stress without apparent cost of ductility.

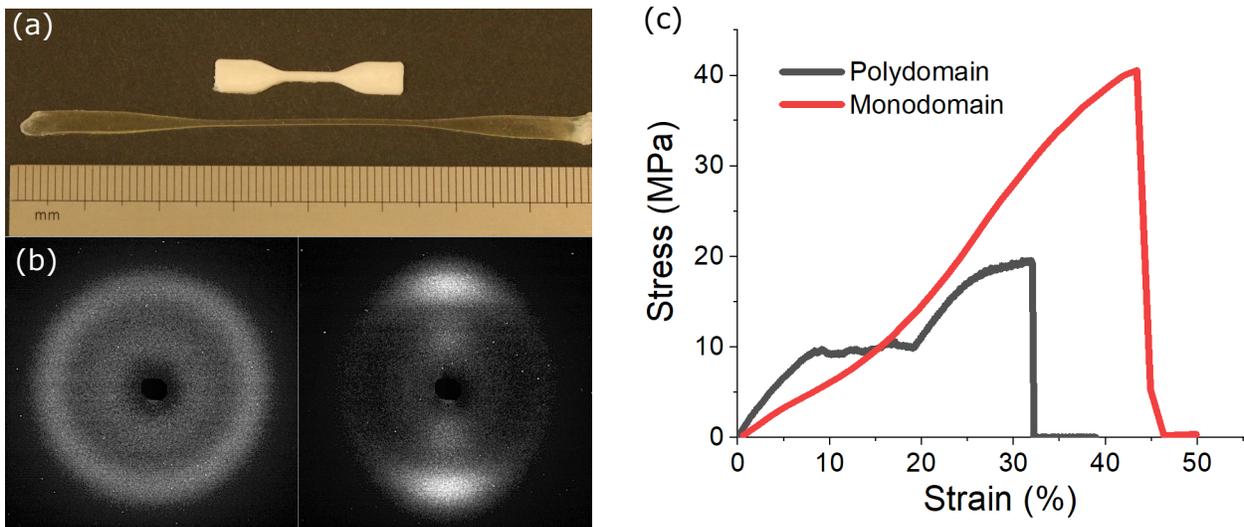


Figure 3: (a) Top: polydomain Si-RM82 sample crosslinked at room temperature without strain imposed, compared to monodomain Si-RM82 (bottom) that is crosslinked when a 200% strain is imposed. (b) The wide-angle x-ray diffraction pattern of polydomain Si-RM82 (left) is compared with the pattern of monodomain Si-RM82 (right), which confirms the mesogen alignment. (c) Both Si-RM82 samples are much stiffer than the base Si-SN (shown later). Polydomain Si-RM82 display a serrated plateau attributed to the breakdown of RM82-SN sacrificial network, while monodomain Si-RM82 does not have such a plateau.

Monodomain Si-RM82 is strong, but its enhancing RM82-SN network does not completely prevent the base Si-SN from its reversible thermal actuation. This, of course, is dependent on the proportion of polyacrylate in the system and we can control it by choosing the optimal concentration of RM82 monomer in toluene solution (20wt%) during the fabrication of Si-

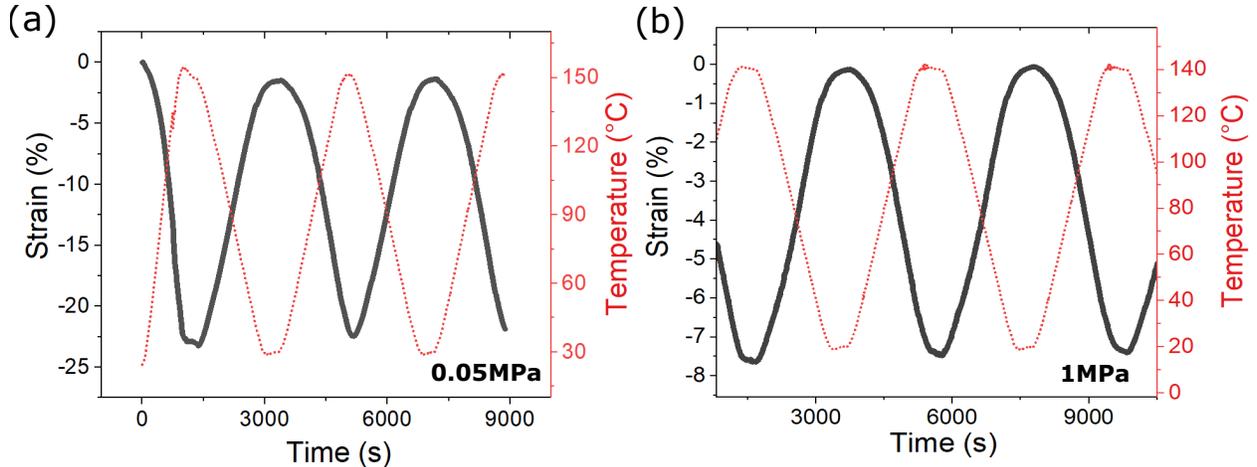


Figure 4: (a) Si-RM82 thermally actuate when under 1MPa and (b) when under stress-free (50kPa to keep taut), heating/cooling rate is $5^{\circ}\text{C}/\text{min}$. The sample display actuation across a large temperature range.

RM82. Figure 4 show monodomain Si-RM82 sample is capable of actuation under load-free conditions, as well as under large tension. An almost 20% of actuation strain is achievable when the sample actuates stress-free, and 8% of strain remains when the sample actuates under stress as large as 1MPa. In addition, we notice that the Si-RM82 system actuates over an unusually large temperature range. To verify this observation, we measured the blocking stress generated when the Si-RM82 is heated at a constant length, see Fig. 5. The profile spans across a large temperature range and it is smoother than the blocking stress profile generated in Si-SN (insert). This feature was not reported in the double networks made by Lu et al. and we accredit it to the retained ordering of RM82-SN network at high temperatures, when the underlying Si-SN becomes isotropic.^{32,46} Due to the enhanced elastic modulus (shown later), the highest blocking stress generated in Si-RM82 is measured be to 3MPa, and the sample does not break at this temperature and stress level. It is a stark contrast to the 0.35MPa in Si-SN which readily breaks down at 100°C .

Since the rigid RM82-SN network we have used so far is made of reactive mesogen monomers which is an anisotropic molecule, we wanted to know if similar observations can be made if we use an isotropic diacrylate monomer to replace RM82. We therefore synthesized a control network labelled as Si-diA, using isotropic diA-SN (shown in Fig.1) as the

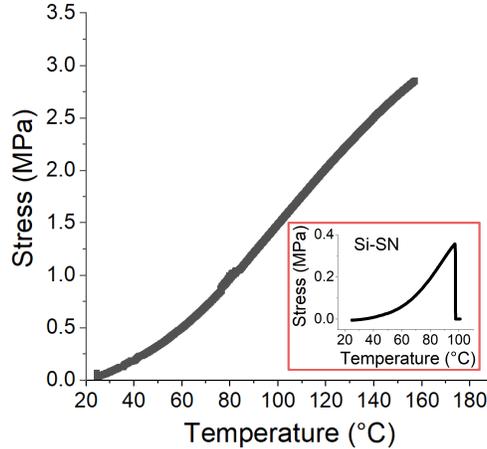


Figure 5: Blocking stress profile (heating rate $3^{\circ}\text{C}/\text{min}$) in Si-RM82 confirms such large actuation temperature range as it has not reach equilibrium at 160°C . Si-RM82 can sustain a large block stress (3MPa) without sample failure. In comparison, Si-SN generates 0.35MPa blocking stress and readily fails at 100°C (inset).

absorbed monomer. In this case, the pre-cured Si-diA sample remains transparent after solvent evaporation, indicating the complete loss of liquid crystalline ordering due to the 20% isotropic impurity added.⁵¹⁻⁵³ It responds to imposed strain like any isotropic elastomer, that is, bouncing back upon release of strain. In short, the diacrylate monomer used in this type of DN-LCE to form the rigid enhancing network needs to be mesogenic, so that it can be aligned with the base LCE network.

Si-TPU double network

Although logically simple, the immersion method is generally sub-optimal: it is time-consuming, it requires multiple intervention steps, and it may suffer from diffusion limitation in the large-size sample. Thus, one-pot reaction is favourable as it allows shorter fabrication time and also scalable. We used a simple one-pot method to fabricate Si-TPU by doping into 50wt% commercial thermoplastic polyurethane (TPU95A) during the initial Si-SN synthesis. Although the polyurethane used here is not crosslinked, for simplicity we also name this type of sample as DN-LCE as they are mechanically not inferior to other DN-LCEs in this report. The resultant Si-TPU is shown to have preserved liquid crystalline phase based on the com-

parison with a control isotropic sample (diBP-TPU), which is made by replacing the base Si-SN network with isotropic diBP-SN.

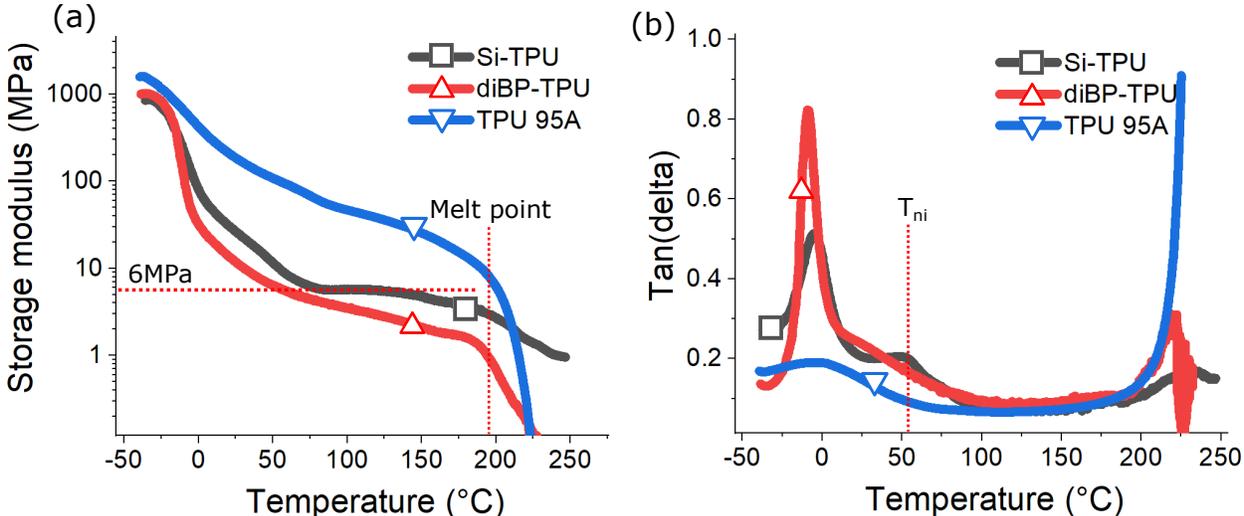


Figure 6: (a) Storage modulus of Si-TPU and diBP-TPU in DMA test, compared to TPU95A. Si-TPU has a relatively stable modulus plateau of 6MPa after its nematic-isotropic transition at around 50°C, while diBP-TPU display a continuous drop of modulus after its glass transition. Both DN-LCEs show a fast decrease of storage modulus at around 200°C due to the melting of crystallite in their contained TPU.

Comparing Si-TPU and diBP-TPU in the DMA test shown in Fig.6(a), Si-TPU has a relatively flat rubbery modulus after its nematic-isotropic transition temperature whilst diBP-TPU shows a continuous drop in modulus. Both samples start to experience a fast drop of storage modulus after temperature passes 200°C due to the melting of TPU they contained(TPU 95A). Figure.6(b) shows the $\tan(\delta)$ of Si-TPU with an extra peak at around 50°C, corresponding to nematic-isotropic transition, while diBP-TPU does not have this feature. This suggests that the liquid crystalline ordering in Si-SN has not been disrupted by the introduction of isotropic TPU. When TPU melts in these DN-LCE at a higher temperatures, the increase of $\tan(\delta)$ in both DN-LCEs is much less pronounced than pure TPU sample, because the interpenetrating Si-SN has helped protect the network's mechanical integrity. Remarkably, and perhaps due to the non-crosslinked nature of TPU, both Si-TPU and diBP-TPU display enormous strain-at-break of around 1500%. Tensile test results shown in Fig.7(a) display such synergy in effect, where the combination of TPU and Si-SN gives

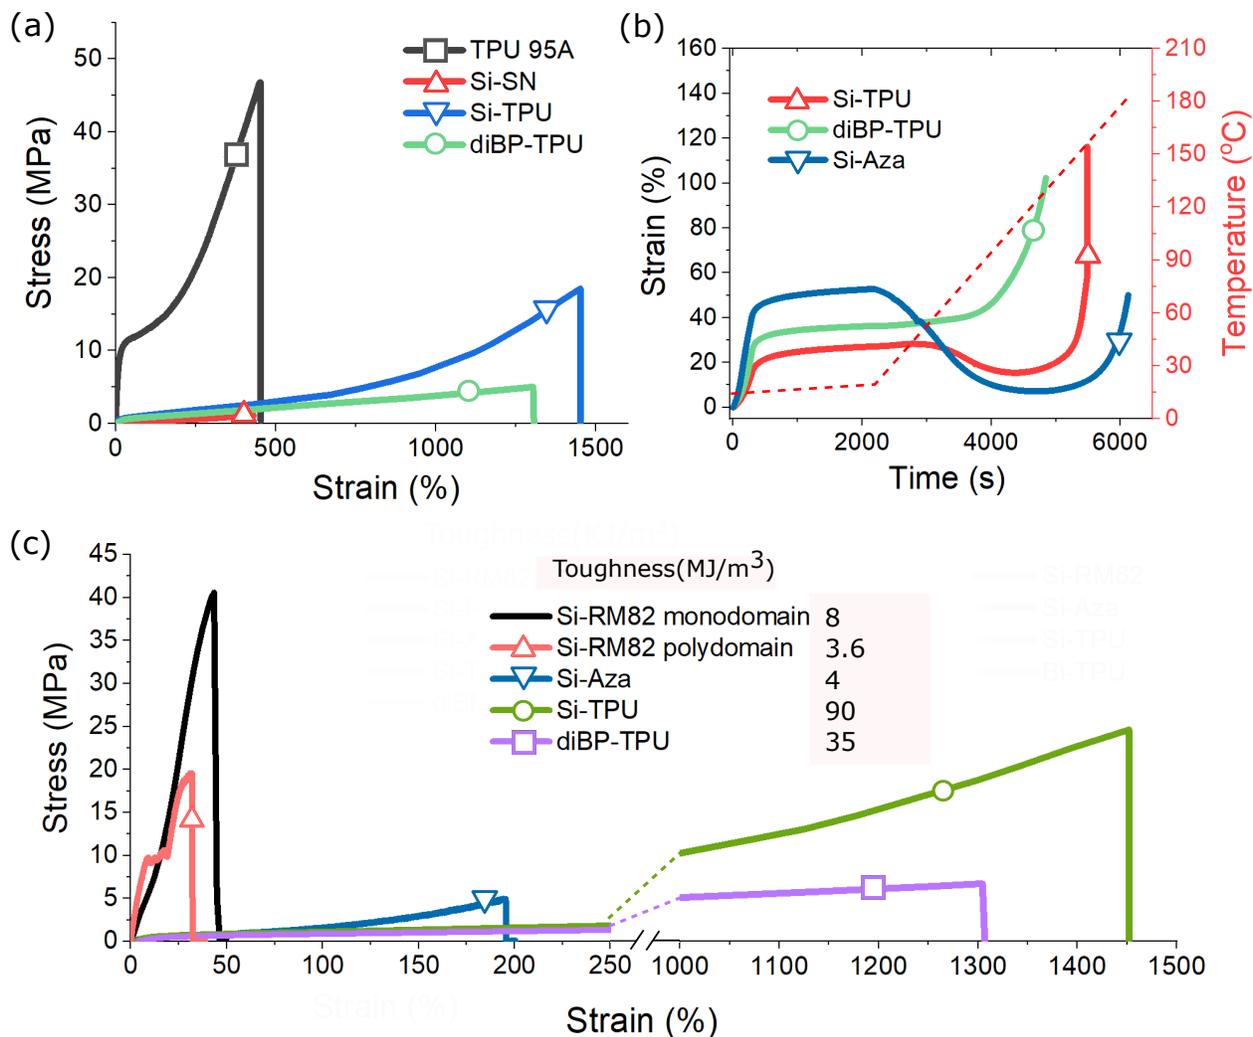


Figure 7: (a) Ambient tensile test of Si-TPU and diBP-TPU in comparison with TPU 95A and Si-SN. Both DN-LCEs show enormous strain-at-break nowhere found from the single networks. (b) Iso-stress test of Si-TPU where it is heated under constant stress of 0.5MPa. Mesogenic Si-TPU shows a 10% actuation strain while the non-mesogenic diBP-TPU does not actuate at all. For comparison, Si-Aza was also tested under the same heating profile but under a lower 0.25MPa, showing a similar pattern of behaviour. (c) Comparison of the stress-strain curves for Si-RM82 (both poly- and monodomain), Si-Aza, Si-TPU, diBP-TPU (all polydomain) and each of their toughness is calculated by measuring the area under curves.

rise to significantly toughness. The plot (c) compares their stress-strain curves with those measured in Si-RM82 and Si-Aza (discussed later). If we calculate DN-LCEs toughness by measuring the area below their stress-strain curves, the toughness of Si-TPU is the largest amongst all fabricated DN-LCEs, reaching 90MJ/m^3 . It is over 10 times the toughness of Si-RM82 (8MJ/m^3) and 20 times of Si-Aza (4MJ/m^3). This is much more than the toughness of single network Si-SN and Aza-SN, which are calculated from Fig.10 to be only 2.3MJ/m^3 and 3.3MJ/m^3 , respectively. We want to point out, that one only expects the toughening effect in Si-TPU prevails at room temperature: at high temperatures, the hydrogen bonding will lose its efficacy.

Since we found that liquid crystalline phase is preserved in the Si-TPU sample, we now want to test whether this type of DN-LCE can thermally actuate. The results of Si-TPU thermal actuation under a constant load is tested by DMA and are shown in Fig.7(b). As expected, Si-TPU can thermally actuate under the stress while its isotropic counterpart diBP-TPU does not show any significant contraction at the same stress. Both double networks start flowing at higher temperatures due to the exchange of siloxane and the melting of TPU. For comparison, Si-Aza was also tested in this way, and the result is also included in Fig.7(b) to show a similar actuation and flowing behaviour. However, despite the complete stress relaxation of Si-TPU is observed in DMA, Fig.8(a), our effort to realign the Si-TPU mesogens at high temperature and program an uniform monodomain have failed, and we could only fabricate Si-TPU in its polydomain state. It is perhaps due to the overwhelmingly present hydrogen bonding that causes constraints in mesogen realignment. In fact, after the addition of TPU, the Si-TPU responds to imposed mechanical strain just like normal isotropic elastomers do (with a clear lack of semi-soft stress plateau) and it remains opaque no matter how much strain was applied. However, if we compare the Si-TPU and Si-diA, both DN-LCEs contain isotropic enhancing networks, Si-TPU still preserves liquid crystalline phase of Si-SN, therefore it can actuate under load, while in Si-diA the original liquid crystalline phase Si-SN is fully destroyed. Therefore, it is logical to attribute such deviation to the local

phase separation in Si-TPU (due to polarity difference of the two constituent networks). Very recently, Gao et al.⁵⁴ described a method to prepare interpenetrating network using thiol-ene nanogel with linear polyurethane network, which shows the phase separation between the two polymers when the thiol-ene network does not contain urethane bond. This observation corresponds to our case quite well. In contrast, in Si-diA the isotropic impurity remains homogeneously dispersed and suppresses the mesogenic order.

Si-Aza double network

We attempted to introduce post-polymerization reprocessability in an another type of DN-LCE system, which is labelled as Si-Aza in Fig. 1. Instead of RM82 monomers absorbed and photo-crosslinked, here we want a different kind of monomer to be absorbed and photo-crosslinked, whose secondary network has a bond exchangeable mechanism different from siloxane exchange in the base network. We considered that RM82/amine is a suitable monomer combination to be absorbed into the swollen Si-SN, as their aza-Michael reaction is slow enough, and the monomers have sufficient time to diffuse into the bulk base Si-SN, which is necessary for homogenization.^{13,19,57-59} By a slight off-stoichiometry, the growing polymer chains can be capped with acrylate end-groups. *In-situ* generated Aza-SN is thus formed by crosslinking the linear polymers after the evaporation of the solvent. Transesterification is the bond-exchange mechanism in this network, and to facilitate its speed we choose an amine chain-extender APD because of the hydroxyl groups it contains.⁶⁰ Indeed, when combined with siloxane exchange from the base Si-SN, the overall Si-Aza is able to fully relax stress at a test temperature of 230°C, Fig.8(a), in contrast to the Si-RM82 double network. We compared the welding behaviour of Si-Aza and Si-RM82 in the hot press, as shown in Fig.8(b), clearly confirming the distinction between an exchangeable Si-Aza network and the thermoset Si-RM82.

The plastic flow behaviour may be attributed to multiple origins in this network: (1) independent siloxane exchange and transesterification in either of the networks, which is

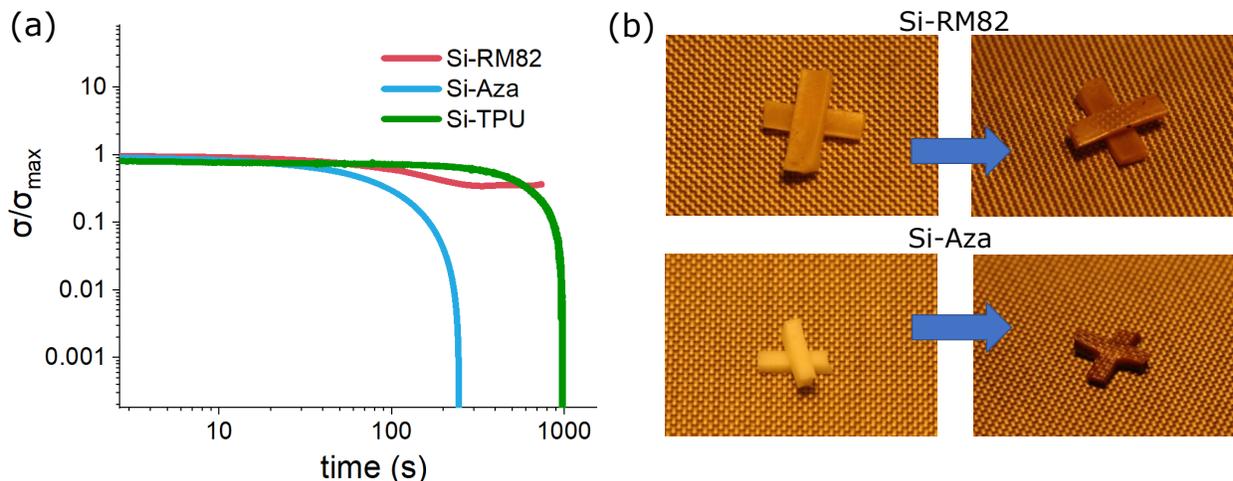


Figure 8: (a) DMA measurement of stress relaxation for the DN-LCEs at 230°C, where Si-Aza and Si-TPU show a complete stress relaxation, while Si-RM82 does not (the Si-TPU system will be introduced later in the text). (b) Both DN-LCEs are cut into pieces and pressed under hot press at 200°C for 1 hour. Si-RM82 does not fuse together, while Si-Aza does.

the ideal scenario that we were hoping to achieve. (2) The additional transesterification across the two networks could occur, because of the additional ester group contained in Si-SN, and thus the two networks can fuse into one. (3) The RM82 mesogen core could break down due to additional transesterification.³⁸ (4) A dissociative (retro) aza-Michael reaction could occur within the network, liquidising it.⁶¹ In fact, the retro aza-Michael is suggestive in our case because we had also tried synthesising Aza-SN using primary amine that does not contain any hydroxyl group, and that network still can be liquidised at high temperatures (200°C). Furthermore, we also noticed that the Si-Aza sample turns brown and significantly reduces its tensile strength after heat treatment at around 200°C, a temperature used for reprocessing (shown in Fig.8(b) and Fig.9). In order to isolate the process, we fabricated Aza-SN that has acrylate in a high 60% excess, so as to stiffen the sample for tensile measurement. The resulting tensile strain-stress curves, with their corresponding ATR-FITR spectra, were recorded before and after the heat treatment at 200°C and shown in Fig.9(a-b). The deterioration of mechanical integrity in the sample is obvious after the heat treatment as short as 20 minutes, and as the extra acrylate peaks have appeared in its

ATR-FTIR spectrum indicating the retro aza-Michael dissociation.

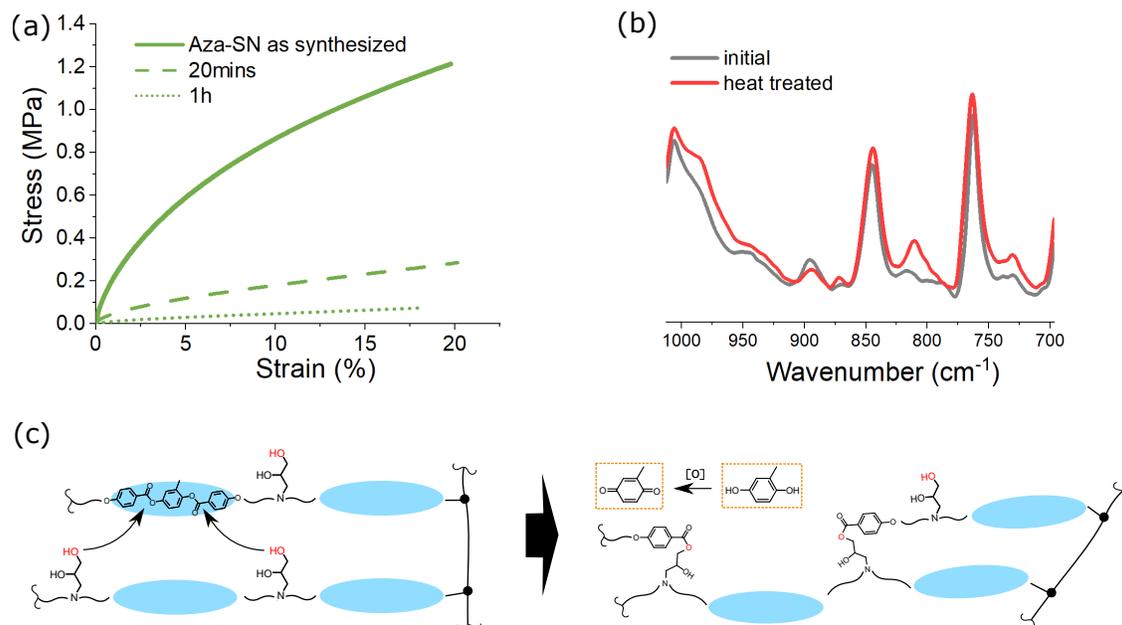


Figure 9: (a) Strain-stress responses of a highly crosslinked Aza-SN, before and after heat treatment at 200°C for the duration indicated. Each sample are subsequently cooled in room temperature for 24 hours prior to the next round of tensile testing. The graph clearly indicates that mechanical deterioration has occurred in Aza-SN network. (b) Additional peaks appear in the ATR-FTIR scans after the sample was thermally treated, indicating that side reactions have occurred. (c) Illustration of possible excessive transesterification that breaks down the mesogenic core. The newly formed diol is then oxidised by air, producing brown color.

If we avoid the possibility of degradation in Si-Aza network by not treating it at high temperatures, the introduction of low-crosslinking density (soft) Aza-SN network into the soft Si-SN provides no sufficient strengthening effect. In fact, Si-Aza is weaker compared to Si-RM82, as shown in Fig.10. Although due to the presence of a physical sacrificial mechanism (i.e. hydrogen bond), Si-Aza manages to reach 5MPa breaking stress, slightly better than that of Si-SN (1MPa) and Aza-SN (3MPa) alone. The mechanical properties of the four samples can be further revealed by dynamic mechanical analysis (DMA), shown in Fig.11. In (a), we have clearly observed variation of isotropic rubbery modulus in different DN-LCEs, with Si-RM82 reaching 22MPa and Si-Aza 3MPa. Both DN-LCEs do not show a clear-cut isotropic transition in high temperatures, which is attributed to the internal

constraint introduced by the secondary network. In comparison, both Si-SN and Aza-SN have a rubbery modulus of around 1MPa after seeing a sharp dip in their modulus at around 70°C, indicating the nematic-isotropic transition. Figure.11(b) is the $\tan(\delta)$ measured from the same samples. We are able to see that all four samples have almost identical nematic-isotropic transition temperatures at around 70°C but the nematic-isotropic peaks on both DN-LCEs are much less obvious than those of single networks. Due to the significant presence of hydrogen bond in Aza-SN, this sample sees an increase of glass transition temperature compared with the rest of the samples.⁶²⁻⁶⁴

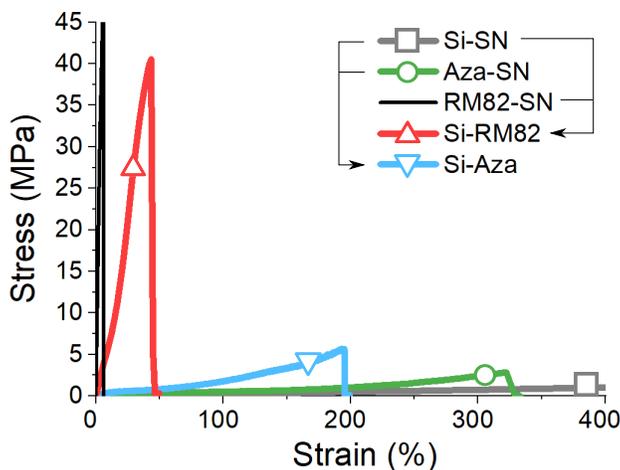


Figure 10: In comparison, Si-RM82 is tougher than its constituent networks: Si-SN and RM82-SN(reproduced from ref.³²). Si-Aza also has a higher breaking stress (5MPa) than its constituent networks, Si-SN (1MPa) and Aza-SN (3MPa), although lower than that of Si-RM82. Si-Aza, Si-SN and Aza-SN sample are all tested in uni-axially tensile machine in their polydomain state, while monodomain Si-RM82 is used.

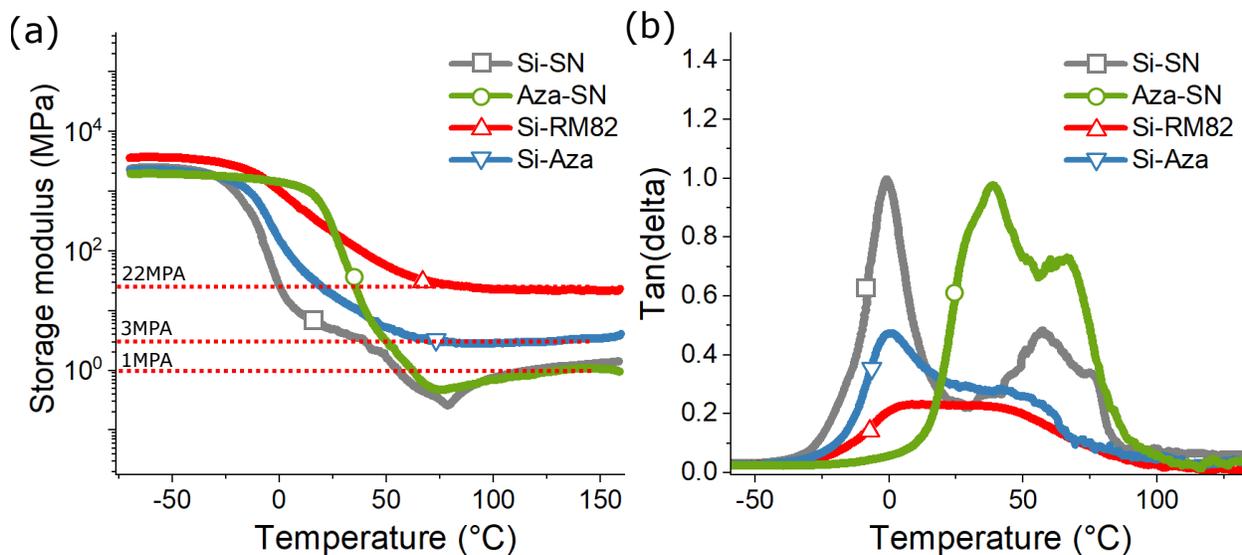


Figure 11: DMA test results of DN-LCEs and single network Si-SN, Aza-SN. (a) Rubbery modulus is measured in the plateau when sample were heated above 70°C. Si-RM82 has a modulus of 22MPa, Si-Aza has a modulus of 3MPa, and both single networks only have a modulus of 1MPa. (b) Tan(δ) of the same samples. While all the samples show nematic-isotropic transition temperature at around 70°C, the transition peaks of DN-LCEs are apparently less obvious than those of single networks.

Conclusion

In this paper, we have described how to use the double network strategy to fabricate mechanically tough DN-LCEs that are capable of thermal actuation. We explored three very different DN-LCEs, which are Si-RM82, Si-TPU, Si-Aza, obtained by immersion or one-pot synthesis methods. The properties of these DN-LCEs were characterised and compared. For Si-RM82, we found how to fabricate the monodomain sample, which can repeatedly thermally actuate, and compared it with its polydomain counterpart. The monodomain Si-RM82 has the highest breaking stress among all DN-LCEs because of the presence of an aligned rigid polyacrylate network. We showed that this polyacrylate network imparts large rubber modulus to the Si-RM82 and in return, increases the blocking stress generated inside Si-RM82 without sample failure. For the thermoplastics double network Si-TPU, we showed that it has a medium tensile strength and modulus among all our DN-LCEs. Despite the uncrosslinked and isotropic nature of the TPU used in this fabrication, Si-TPU

shows a remarkably large strain-at-break, hence at room temperature it gives an enormous sample toughness. We also discovered that the Si-TPU is able to thermally actuate under stress, and we discussed the question of why the addition of non-mesogenic impurity does not adversely affect the liquid crystalline ordering in the Si-TPU network, as it does in Si-diA. However, the introduction of thermoplastic polyurethane makes this type of DN-LCE not able to be realigned thus not reprogrammable. For the exchangeable Si-Aza, we fabricated the LCE sample by generating a low-crosslinking-density liquid crystalline polymer *in-situ*, and showed that the sample is able to flow at high temperature and fully relax the externally applied stress. However, the sample sees the lowest tensile strength among all our DN-LCEs due to smaller secondary crosslinking density. We also found the undesired side-reactions that occurred in Si-Aza that cause degradation of mesogens and the network. Through this paper, we demonstrated that the double networks strategy can be employed in making DN-LCEs to improve the mechanical proprieties of LCEs and impart very different characteristics depending on the enhancing network selected.

Acknowledgement

The authors thank Mohand Saed and Alexandra Gablier for useful communications and support. This work was supported by the ERC H2020 Advanced grant 768659.

References

- (1) M. Warner and E. M. Terentjev, *Liquid Crystal Elastomers*; Oxford University Press, 2003; p 154.
- (2) Yuan, C.; Roach, D. J.; Dunn, C. K.; Mu, Q.; Kuang, X.; Yakacki, C. M.; Wang, T. J.; Yu, K.; Qi, H. J. 3D printed reversible shape changing soft actuators assisted by liquid crystal elastomers. *Soft Matter* **2017**, *13*, 5558–5568.

- (3) Lahikainen, M.; Zeng, H.; Priimagi, A. Reconfigurable photoactuator through synergistic use of photochemical and photothermal effects. *Nat. Commun.* **2018**, *9*, 1–8.
- (4) Palagi, S.; Mark, A. G.; Reigh, S. Y.; Melde, K.; Qiu, T.; Zeng, H.; Parmeggiani, C.; Martella, D.; Sanchez-Castillo, A.; Kapernaum, N.; Giesselmann, F.; Wiersma, D. S.; Lauga, E.; Fischer, P. Structured light enables biomimetic swimming and versatile locomotion of photoresponsive soft microrobots. *Nat. Mater.* **2016**, *15*, 647–653.
- (5) Guin, T.; Settle, M. J.; Kowalski, B. A.; Auguste, A. D.; Beblo, R. V.; Reich, G. W.; White, T. J. Layered liquid crystal elastomer actuators. *Nat. Commun.* **2018**, *9*, 1–7.
- (6) Nocentini, S.; Martella, D.; Wiersma, D. S.; Parmeggiani, C. Beam steering by liquid crystal elastomer fibres. *Soft Matter* **2017**, *13*, 8590–8596.
- (7) He, Q.; Wang, Z.; Wang, Y.; Minori, A.; Tolley, M. T.; Cai, S. Electrically controlled liquid crystal elastomer-based soft tubular actuator with multimodal actuation. *Sci. Adv.* **2019**, *5*, 1–8.
- (8) Küpfer, J.; Finkelmann, H. Nematic liquid single crystal elastomers. *Macromol. Rapid Commun.* **1991**, *12*, 717–726.
- (9) Tajbakhsh, A. R.; Terentjev, E. M. Spontaneous thermal expansion of nematic elastomers. *Eur. Phys. J. E* **2001**, *6*, 181–188.
- (10) Clarke, S. M.; Hotta, A.; Tajbakhsh, A. R.; Terentjev, E. M. Effect of cross-linker geometry on dynamic mechanical properties of nematic elastomers. *Phys. Rev. E* **2002**, *65*, 021804.
- (11) Saed, M. O.; Volpe, R. H.; Traugott, N. A.; Visvanathan, R.; Clark, N. A.; Yakacki, C. M. High strain actuation liquid crystal elastomers via modulation of mesophase structure. *Soft Matter* **2017**, *13*, 7537–7547.

- (12) Traugutt, N. A.; Volpe, R. H.; Bollinger, M. S.; Saed, M. O.; Torbati, A. H.; Yu, K.; Dadivanyan, N.; Yakacki, C. M. Liquid-crystal order during synthesis affects main-chain liquid-crystal elastomer behavior. *Soft Matter* **2017**, *13*, 7013–7025.
- (13) Kotikian, A.; Truby, R. L.; Boley, J. W.; White, T. J.; Lewis, J. A. 3D printing of liquid crystal elastomeric actuators with spatially programmed nematic order. *Adv. Mater.* **2018**, *30*, 1–6.
- (14) Haines, C. S. et al. Artificial muscles from fishing line and sewing thread. *Science* **2014**, *343*, 868–872.
- (15) Mohd Jani, J.; Leary, M.; Subic, A.; Gibson, M. A. A review of shape memory alloy research, applications and opportunities. *Mater. Des.* **2014**, *56*, 1078–1113.
- (16) Rothmund, P.; Kellaris, N.; Mitchell, S. K.; Acome, E.; Keplinger, C. HASEL artificial muscles for a new generation of lifelike robots—recent progress and future opportunities. *Adv. Mater.* **2020**, *33*, 2003375.
- (17) Volpe, R. H.; Mistry, D.; Patel, V. V.; Patel, R. R.; Yakacki, C. M. Dynamically crystallizing liquid-crystal elastomers for an expandable endplate-conforming interbody fusion cage. *Adv. Healthc. Mater.* **2020**, *9*, 1–10.
- (18) Ahir, S. V.; Tajbakhsh, A. R.; Terentjev, E. M. Self-assembled shape-memory fibers of triblock liquid-crystal polymers. *Adv. Func. Mater.* **2006**, *16*, 556–560.
- (19) Yoon, H. H.; Kim, D. Y.; Jeong, K. U.; Ahn, S. K. Surface aligned main-chain liquid crystalline elastomers: Tailored properties by the choice of amine chain extenders. *Macromolecules* **2018**, *51*, 1141–1149.
- (20) Yan, M.; Tang, J.; Xie, H. L.; Ni, B.; Zhang, H. L.; Chen, E. Q. Self-healing and phase behavior of liquid crystalline elastomer based on a block copolymer constituted of a

- side-chain liquid crystalline polymer and a hydrogen bonding block. *J. Mater. Chem. C* **2015**, *3*, 8526–8534.
- (21) Zou, W.; Lin, X.; Terentjev, E. M. Amine-acrylate liquid single crystal elastomers reinforced by hydrogen bonding. *Adv. Mater.* **2021**, *33*, 2101955.
- (22) Mamiya, J. I.; Yoshitake, A.; Kondo, M.; Yu, Y.; Ikeda, T. Is chemical crosslinking necessary for the photoinduced bending of polymer films? *J. Mater. Chem.* **2008**, *18*, 63–65.
- (23) Ban, J.; Mu, L.; Yang, J.; Chen, S.; Zhuo, H. New stimulus-responsive shape-memory polyurethanes capable of UV light-triggered deformation, hydrogen bond-mediated fixation, and thermal-induced recovery. *J. Mater. Chem. A* **2017**, *5*, 14514–14518.
- (24) Zhao, X. Multi-scale multi-mechanism design of tough hydrogels: Building dissipation into stretchy networks. *Soft Matter* **2014**, *10*, 672–687.
- (25) Chen, Q.; Chen, H.; Zhu, L.; Zheng, J. Fundamentals of double network hydrogels. *J. Mater. Chem. B* **2015**, *3*, 3654–3676.
- (26) Yuk, H.; Zhang, T.; Lin, S.; Parada, G. A.; Zhao, X. Tough bonding of hydrogels to diverse non-porous surfaces. *Nat. Mater.* **2016**, *15*, 190–196.
- (27) Gong, J. P.; Katsuyama, Y.; Kurokawa, T.; Osada, Y. Double-network hydrogels with extremely high mechanical strength. *Adv. Mater.* **2003**, *15*, 1155–1158.
- (28) Ducrot, E.; Chen, Y.; Bulters, M.; Sijbesma, R. P.; Creton, C. Toughening elastomers with sacrificial bonds and watching them break. *Science* **2014**, *344*, 186–189.
- (29) Ube, T.; Takado, K.; Ikeda, T. Photomobile materials with interpenetrating polymer networks composed of liquid-crystalline and amorphous polymers. *J. Mater. Chem. C* **2015**, *3*, 8006–8009.

- (30) Hoekstra, D. C.; Debije, M. G.; Schenning, A. Triple-shape-memory soft actuators from an interpenetrating network of hybrid liquid crystals. *Macromolecules* **2021**, *54*, 5410–5416.
- (31) Stumpel, J. E.; Gil, E. R.; Spoelstra, A. B.; Bastiaansen, C. W.; Broer, D. J.; Schenning, A. P. Stimuli-responsive materials based on interpenetrating polymer liquid crystal hydrogels. *Adv. Func. Mater.* **2015**, *25*, 3314–3320.
- (32) Lu, H. F.; Wang, M.; Chen, X. M.; Lin, B. P.; Yang, H. Interpenetrating liquid-crystal polyurethane/polyacrylate elastomer with ultrastrong mechanical property. *J. Am. Chem. Soc.* **2019**, *141*, 14364–14369.
- (33) Kloxin, C. J.; Scott, T. F.; Adzima, B. J.; Bowman, C. N. Covalent adaptable networks (CANs): A unique paradigm in cross-linked polymers. *Macromolecules* **2010**, *43*, 2643–2653.
- (34) Montarnal, D.; Capelot, M.; Tournilhac, F.; Leibler, L. Silica-like malleable materials from permanent organic networks. *Science* **2011**, *334*, 965–968.
- (35) Pei, Z.; Yang, Y.; Chen, Q.; Terentjev, E. M.; Wei, Y.; Ji, Y. Mouldable liquid-crystalline elastomer actuators with exchangeable covalent bonds. *Nat. Mater.* **2014**, *13*, 36–41.
- (36) Saed, M. O.; Gablier, A.; Terentjev, E. M. Exchangeable liquid crystalline elastomers and their applications. *Chem. Rev.* **2021**, <https://doi.org/10.1021/acs.chemrev.0c01057>.
- (37) Gablier, A.; Saed, M. O.; Terentjev, E. M. Transesterification in epoxy-thiol exchangeable liquid crystalline elastomers. *Macromolecules* **2020**, *53*, 8642–8649.
- (38) Hanzon, D. W.; Traugutt, N. A.; McBride, M. K.; Bowman, C. N.; Yakacki, C. M.;

- Yu, K. Adaptable liquid crystal elastomers with transesterification-based bond exchange reactions. *Soft Matter* **2018**, *14*, 951–960.
- (39) Ube, T.; Kawasaki, K.; Ikeda, T. Photomobile liquid-crystalline elastomers with rearrangeable networks. *Adv. Mater.* **2016**, 8212–8217.
- (40) Saed, M. O.; Gablier, A.; Terentjev, E. M. Liquid crystalline vitrimers with full or partial boronic-ester bond exchange. *Adv. Funct. Mater.* **2020**, *30*, 1–8.
- (41) Saed, M. O.; Terentjev, E. M. Siloxane crosslinks with dynamic bond exchange enable shape programming in liquid-crystalline elastomers. *Sci. Rep.* **2020**, *10*, 17–19.
- (42) Wen, Z.; McBride, M. K.; Zhang, X.; Han, X.; Martinez, A. M.; Shao, R.; Zhu, C.; Visvanathan, R.; Clark, N. A.; Wang, Y.; Yang, K.; Bowman, C. N. Reconfigurable LC elastomers: Using a thermally programmable monodomain to access two-way free-standing multiple shape memory polymers. *Macromolecules* **2018**, *51*, 5812–5819.
- (43) Wang, Z.; Tian, H.; He, Q.; Cai, S. Reprogrammable, reprocessable, and self-healable liquid crystal elastomer with exchangeable disulfide bonds. *ACS Appl. Mater. Interfaces.* **2017**, *9*, 33119–33128.
- (44) McBride, M. K.; Martinez, A. M.; Cox, L.; Alim, M.; Childress, K.; Beiswinger, M.; Podgorski, M.; Worrell, B. T.; Killgore, J.; Bowman, C. N. A readily programmable, fully reversible shape-switching material. *Sci. Adv.* **2018**, *4*, eaat4634.
- (45) Herbert, K. M.; Fowler, H. E.; McCracken, J. M.; Schlafmann, K. R.; Koch, J. A.; White, T. J. Synthesis and alignment of liquid crystalline elastomers. *Nature Reviews Materials* **2021**,
- (46) Dierking, I. Polymer network-stabilized liquid crystals. *Adv. Mater.* **2000**, *12*, 1521–4095.

- (47) Yang, D.-K.; Chien, L.-C.; Doane, J. W. Polymer networks formed in liquid crystals. *Appl. Phys. Lett.* **1992**, *60*, 3102–3109.
- (48) Fung, Y. K.; Yang, D. K.; Ying, S.; Chien, L. C.; Zumer, S.; Doane, J. W. Polymer networks formed in liquid crystals. *Liq. Crys.* **1995**, *19*, 797–801.
- (49) Sano, K.; Ishida, Y.; Aida, T. Synthesis of anisotropic hydrogels and their applications. *Angew. Chem.* **2018**, *57*, 2532–2543.
- (50) Gong, J. P. Why are double network hydrogels so tough? *Soft Matter* **2010**, *6*, 2583–2590.
- (51) Jana, P. K.; Lam, J.; Mangal, R.; Alava, M. J.; Parveen, N.; Laurson, L. Impurity-induced nematic-isotropic transition of liquid crystals. *Phys. Chem. Chem. Phys.* **2021**, *23*, 8825–8835.
- (52) Denolf, K.; Cordoyiannis, G.; Glorieux, C.; Thoen, J. Effect of nonmesogenic impurities on the liquid crystalline phase transitions of octylcyanobiphenyl. *Phys. Rev. E* **2007**, *76*, 051702.
- (53) Lin, X.; Saed, M. O.; Terentjev, E. M. Continuous spinning aligned liquid crystal elastomer fibers with a 3D printer setup. *Soft Matter* **2021**, *17*, 5436–5443.
- (54) Gao, G.; Wang, X.; Chen, M.; Bowman, C. N.; Stansbury, J. W. Functional Nanogels as a Route to Interpenetrating Polymer Networks with Improved Mechanical Properties. *Macromolecules* **2021**, doi: 10.1021/acs.macromol.1c01242.
- (55) West, J. L. Phase separation of liquid crystals in polymers. *Mol. Cryst. Liq. Cryst.* **1988**, *157*, 427–441.
- (56) Dierking, I. *Polymer-modified Liquid Crystals*; RSC, 2012; pp 19–36.

- (57) Retailleau, M.; Ibrahim, A.; Croutxé-Barghorn, C.; Allonas, X.; Ley, C.; Le Nouen, D. One-pot three-step polymerization system using double click michael addition and radical photopolymerization. *ACS Macro Lett.* **2015**, *4*, 1327–1331.
- (58) Liu, Y.; Li, Y.; Keskin, D.; Shi, L. Poly(β -Amino Esters): Synthesis, formulations, and their biomedical applications. *Adv. Healthc. Mater.* **2019**, *8*, 1–24.
- (59) Ahn, S. K.; Ware, T. H.; Lee, K. M.; Tondiglia, V. P.; White, T. J. Photoinduced topographical feature development in blueprinted azobenzene-functionalized liquid crystalline elastomers. *Adv. Funct. Mater.* **2016**, *26*, 5819–5826.
- (60) Han, J.; Liu, T.; Hao, C.; Zhang, S.; Guo, B.; Zhang, J. A catalyst-free epoxy vitrimer system based on multifunctional hyperbranched polymer. *Macromolecules* **2018**, *51*, 6789–6799.
- (61) Taplan, C.; Guerre, M.; Prez, F. E. D. Covalent Adaptable Networks Using \hat{I}^2 -Amino Esters as Thermally Reversible Building Blocks. *Journal of the American Chemical Society* **2021**, *143*.
- (62) Wang, R.; Pellerin, C.; Lebel, O. Role of hydrogen bonding in the formation of glasses by small molecules: A triazine case study. *J. Mater. Chem.* **2009**, *19*, 2747–2753.
- (63) Sman, R. G. V. D. Predictions of glass transition temperature for hydrogen bonding biomaterials. *J. Phys. Chem. B* **2013**, *117*, 16303–16313.
- (64) Feldstein, M. M.; Roos, A.; Chevallier, C.; Creton, C.; Dormidontova, E. E. Relation of glass transition temperature to the hydrogen bonding degree and energy in poly(N-vinyl pyrrolidone) blends with hydroxyl-containing plasticizers. *Polymer* **2003**, *44*, 1819–1834.