

THz nanoscopy of plasmonic resonances with a quantum cascade laser

Riccardo Degl'Innocenti, Robert Wallis, Binbin Wei, Long Xiao, Stephen J Kindness, Oleg Mitrofanov, Philipp Braeuninger-Weimer, Stephan Hofmann, Harvey E Beere, and David A. Ritchie
ACS Photonics, **Just Accepted Manuscript** • DOI: 10.1021/acsphotonics.7b00687 • Publication Date (Web): 28 Aug 2017

Downloaded from <http://pubs.acs.org> on August 29, 2017

Just Accepted

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a free service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are accessible to all readers and citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.

THz nanoscopy of plasmonic resonances with a quantum cascade laser

Riccardo Degl'Innocenti^{1,§}, Robert Wallis^{1,§}, Binbin Wei¹, Long Xiao^{1,2}, Stephen J. Kindness¹, Oleg Mitrofanov³, Philipp Braeuninger-Weimer², Stephan Hofmann², Harvey E. Beere¹, David A. Ritchie¹

¹*Cavendish Laboratory, University of Cambridge, J. J Thomson Avenue, CB3 0HE Cambridge, United Kingdom*

²*Department of Engineering, University of Cambridge, J. J. Thomson Avenue, CB3 0FA Cambridge, United Kingdom*

³*Department of Electronic and Electrical Engineering, University College London, Torrington Place, WC1E 7JE London, United Kingdom*

[§] *These authors equally contributed*

Abstract: We present a THz scattering near field optical microscope (s-SNOM) based on a quantum cascade laser implemented both as source and detector in a self-mixing scheme utilizing resonant quartz tuning forks as a sensitive nano-positioning element. The home-made s-SNOM, based on a resonant tuning fork and metallic tip, operates in tapping mode with a spatial resolution of ~78 nm. The quantum cascade laser is realized from a bound-to-continuum active region design with a central emission of ~2.85 THz, which has been lens-coupled in order to maximize the feedback into the laser cavity. Accordingly, the spatial resolution corresponds to $>\lambda/1000$. The s-SNOM has been used to investigate a bi-dimensional plasmonic photonic crystal and to observe the plasmonic resonances supported by coupled plasmonic planar antennas, showing remarkable agreement with the theoretical predictions. The compactness, unique sensitivity and fast acquisition capability of this approach makes the proposed s-SNOM a unique tool for solid-state investigations and biomedical imaging.

Keywords: Near-field microscopy, terahertz, plasmonics, photonic crystals, quantum cascade laser, self-mixing detection

The terahertz (THz) frequency range, 0.1-10 THz, lies in the millimetre and sub-millimetre wavelength range of the electromagnetic spectrum and represents a fast-evolving research area. The increasing efforts in THz science and technology are driven by many fields where such radiation finds applications, mainly in communications, spectroscopy and imaging [1,2]. In particular, THz imaging is appealing in several areas. In biomedical research field this non-ionizing radiation has been used for diagnostics, due to its capability of discriminating between healthy and cancerous tissues [3]. Near-field imaging techniques have great potential in many applications, ranging from the investigation of the optical properties of solid-state and two-dimensional materials [4-6] to the excitation and direct retrieval of plasmonic resonant modes [8-11]. In semiconductor physics, THz radiation has proved to be a viable tool for inspection of integrated devices with sub-wavelength resolution [7]. It is well known that THz radiation is sensitive to the doping level of semiconductor devices. Accordingly, it can be implemented for the inspection and mapping of quantum objects even when covered by a dielectric layer, as an alternative and/or complementary technique to photoluminescence techniques. The most commonly used scattering near-field systems are based on modified atomic force microscopes or commercially available instruments, and have proved themselves as efficient tools for the direct mapping and excitation of resonant plasmonic modes in the mid-infrared spectral range [8-10]. Bi-dimensional materials such as topological insulators [12] or graphene [13] are known to also support surface plasmons in the THz range. Graphene has also been proposed as the basic building block of integrated circuitry [14]. However, the direct excitation of surface plasmons is hindered by the wavevector mismatch between the incoming radiation and the supported modes, and typically requires direct patterning or prism-coupling schemes. Near-field microscope probes directly interact with the surface of the object of study through evanescent waves, thus naturally overcoming the dispersion difference. Near field microscopy thus provides a valuable tool for the excitation of all-plasmonic or hybrid devices. The design of future THz integrated optoelectronic devices, such as amplitude [15-17], frequency [18] and polarization [19] modulators, or detectors [20-22], based on metamaterial/plasmonic subwavelength resonances, relies on the detailed analysis of the properties of a single unit, rather than on ensemble averages, thus enforcing the need for a subwavelength inspection tool. Near-field microscopes operating in the THz normally implement cumbersome and unstable gas lasers as sources, such as a CH₃OH laser pumped by a CO₂ laser [7,11]. Quantum cascade

lasers (QCLs) [23] are a more compact, stable and versatile source to be used in these arrangements. The use of QCLs in aperture [24, 25] and apertureless [26] scanning near field optical microscopes has already been reported with a resolution $> 1 \mu\text{m}$ as a proof of principle, without an efficient tip/surface feedback system. The self-mixing scheme represents an elegant and powerful approach to THz detection [27-29]. Instead of using slow-responding and/or cryogenic devices such as pyroelectric or Si-bolometer for detection, self-mixing is based on the perturbation introduced by the radiation scattered into the laser cavity by the tip/surface system. By monitoring the change in bias applied to the QCL, or the QCL power, it is possible to retrieve information about the amplitude and phase of the scattered electric field. This approach presents many advantages over conventional techniques. It allows a more compact scheme, by eliminating the need for extra components. It is an extremely sensitive detection scheme which has been reported to be sensitive to nW power levels [27], thus making it extremely suitable for the detection of intrinsically weak, omnidirectional scattered signals. Finally, it is a fast detection scheme [29], since the ultimate limit is given by the QCL laser dynamics, which typically take place on time scales of picoseconds. The quartz resonant tuning forks (QTF) have been implemented in near field microscopy as an alternative to the atomic force microscope cantilevers [30-32]. The resonances supported by these economic and compact elements are based on the piezoelectric effect. Accordingly, a mechanical modification of the resonance amplitude, frequency or phase translates into a current/voltage change which then provides the feedback mechanism. Because of their high Q-factor and superior stiffness compared to cantilevers, the QTFs are implemented together with sharp metallic tips as an efficient sensitive element in near-field microscopy for the achievement of a constant distance between tip and surface. Their simple circuitry and the lack of an optical illumination feedback system, as required by the cantilever approach, make them the most favourable choice in cryogenic environments [33,34] or in imaging systems susceptible to being optically perturbed.

Results and Discussion: Here, we report a THz s-SNOM system with a resolution of $\sim 78 \text{ nm}$, based on a self-mixing detection scheme and implementing QCLs emitting around 2.85 THz as the source /detector. This home-made system has been used to image the plasmonic resonances supported by a bi-dimensional photonic crystal triangular hole array [35] and the electric field enhancement supported in the gap of a graphene/plasmonic antenna THz detector [21].

The QCL fabrication and coupling to a Silicon lens is described in the Methods section. A schematic of the experimental setup is showed in Fig. 1 a). The laser light is collimated and focused by two 2 inch f/1 off-axis parabolic mirrors with $\sim 30^\circ$ incident angle. When the beam is illuminating the metallic tip, a positive change in the laser power is detected. The apparatus is then arranged for the collection of the scattered light. The self-mixing scheme used for the acquisition of the THz scattered light is reported in Fig. 1 b). To amplify the small voltage perturbation on the laser bias V_{QCL} caused by the scattered light V_{scatt} , it is first mixed with the bias of an identical pulser V_{Ref} synchronized to the repetition rate of the QCL f_{QCL} , kept fixed to 2 kHz. The voltage difference between the two pulsers V_1 and V_2 in Fig. 1 a) was kept as low as possible in order to use the minimum sensitivity scale on the lock-in amplifier, thus minimizing the noise. The voltage difference has been magnified in Fig. 1 b) for clarity. The difference in voltage is then amplified and fed to the lock-in amplifier which has the resonant frequency of the tuning fork f_{rf} as reference. The tuning forks used had a typically resonant frequency of $\sim 30 \text{ kHz}$. A higher feedback in the laser cavity corresponds to a reduced bias measured on the QCL, as schematically showed in Fig. 1 b) and experimentally presented in Fig. S1. A metallic tip with radius $< 50 \text{ nm}$ is mounted in tapping mode configuration. Further details on the set-up and the data acquisition procedure are reported in the Methods section. A typical measurement example is showed in Fig. 2. This picture reports a) the topography, b) the THz scattered image and c) the optical micrograph of the sample, which consisted of metallic features over a SiO_2 substrate. The sample has two overlapping metallic areas achieved with optical lithography, a vertical stripe (Ti/Au, nominal thickness 10/500 nm) and with an electron beam lithography horizontal stripe (Ti/Au nominal thickness 80/20 nm). According to the standard scattering theory, as presented in [36-38] the tip-surface system is modeled as a spherical particle above a planar surface. The incident light induces a dipole in the tip which is mirrored into the substrate, and the combined dipole-system irradiates with an effective polarizability α_{eff} given by Eq. 1:

$$\alpha_{eff} = \frac{\alpha(1+\beta)}{1 - \left(\frac{\alpha\beta}{16\pi(a+z)^3}\right)} \quad (1)$$

Where $\alpha=4\pi a^3(\epsilon_{tip}-1)/(\epsilon_{tip}+2)$, $\beta=(\epsilon_{sub}-1)/(\epsilon_{sub}+1)$, a is the radius of the tip's apex, z is the relative distance between sample and substrate and ϵ_{tip} , ϵ_{sub} are the dielectric constant of the tip and substrate, respectively. Assuming a value for the real part of the dielectric constant ϵ_{sub} of 3.9 for the SiO₂ and of -10,000 [39,40] for the Au features, an ϵ_{tip} of -40,000 [41] for the W-tip having an apex radius of ~30 nm, the model predicts a reduced polarizability, hence scattering efficiency, for a dielectric substrate with respect to a metallic one. The THz image presented in Fig. 2 b) shows comparable values for the scattering signals on the SiO₂ and the thicker Au evaporation. According to the polarizability values calculated using Eq. 1 and reported in Fig. S2 in the SI, the ratio between the polarizability, and hence the scattering, yielded by the two different surfaces is ~1.3. The THz signal recorded over the metallic evaporation obtained via ebeam lithography, corresponding to the horizontal stripe, presents a significantly increased signal in comparison with the thick metal evaporation area and the SiO₂ area. This is attributed to the increased roughness, as also shown by the topography, and uniformity of this area. The induced dipole itself and the tip radius have sizes comparable to the roughness and to the total thickness of this metallic layer which might interact efficiently with the total scattering.

A second scan over the bottom area of Fig. 2 has been recorded with a 100 nm step-size and the topography and corresponding THz signal are reported in Fig. 3 a) and b), respectively. Several profiles have been extracted from the dashed area of Fig. 3 b), to measure the resolution, which, as shown in Fig. 3 c), was calculated to be ~78 nm, by using the 10%-90% criterion. This corresponds to a spatial resolution of ~ $\lambda/1200$, which is comparable to the resolution achieved at these frequencies with a methanol gas laser [7], but obtained with an emitting source with < mW emitting power and without the need of an extra detecting element. At the same time, this system yielded an improvement of more than 10 times compared to similar near-field systems implementing THz QCLs [24,25].

The THz s-SNOM system was then used for mapping the plasmonic resonances supported by resonant metallic features. A surface emitting photonic crystal (SEPHC) QCL [35] based on triangular arrays of holes and emitting around 2.85 THz was chosen since its emission overlapped well with the s-SNOM frequency. The interest in this sample, which was used as a passive element at room temperature, stems from its patterned metallic top contact area, and the relative plasmonic resonances supported. A scanning electron microscope (SEM) micrograph of the top contact of the SEPHC is shown in Fig. 4 a). The patterned metallic surface of the QCL supports dipole modes, as shown in the normalized E-field reported in Fig. 4 b) simulated with the Comsol Multiphysics finite element commercial software following a procedure already explained in [16-17]. The simulated resonant plasmonic modes supported at 2.8 THz have two distinct peaks along the direction of the incident E-field. Fig. 4 c) and d) report the topography and the retrieved THz scattered signal acquired simultaneously together with the respective profiles extracted along the two corresponding lines. The topography is consistent with the SEM picture and the profiles acquired along the two directions, showing the ~0.6 μ m thick metal triangular lattice of holes along the two directions. The image has been smoothed over 3 points and in some points the tip lost contact with the surface, resulting in missing rows, which have been substituted with the first neighbouring points. This operation did not affect the THz signal and also had marginal effects on the topography, as shown by the original data reported in the additional data folder. Because of the lift off the borders of the holes opened on the metallic surface present significant sharp ripples, as showed by the SEM of the inset in Fig. 4 a) and correctly recorded by the topography in Fig. 4 c). The THz image and the corresponding profiles, shown in Fig. 4 d), in contrast to the topography, exhibit an asymmetry in the vertical direction with respect to the horizontal one. In particular, two annular peaks are evident along the polarization direction, in good agreement with the simulations presented in Fig. 4 b). This is consistent with the resonant plasmonic modes supported by the photonic crystal metallic structure. However, due to the sharp metallic rim in the fabrication of the triangular hole array, the THz scattered signal is also strongly influenced by the scanning direction. This can provide an additional signal which is likely to be the predominant effect for this specific sample. Because of the irregular metallic border, an increase in the vertical movement of the tip during the scan translates into an increased proximity of the tip and consequently a stronger scattering signal

1
2
3 compared to smoother scanning paths, as shown in the SI in Fig. S2. This uniquely sensitive approach
4 also allows the retrieval of dielectric/plasmonic modes supported in buried resonant structures at these
5 frequencies, such as the one shown in Fig. 5.

6 A plasmonic antenna array loaded with graphene was chosen as the object of investigation, similar to
7 the devices already investigated for the bolometric detection of THz QCLs in [21], but having a
8 resonant frequency centered around 2.9 THz. The single unit element of the array is composed of
9 planar metallic antennas of size $15 \times 2 \mu\text{m}^2$, fabricated on top of a SiO_2/Si substrate and shorted by
10 graphene regions with $3 \mu\text{m}^2$ area. All the resonant elements are encapsulated in an Al_2O_3 dielectric
11 film up to 100 nm thick deposited by atomic layer deposition. In contrast to the previous device, this
12 presents a smoother metallic border, and the encapsulation with the dielectric layer of Al_2O_3 removed
13 the possibility of any other source of extra scattering. The gap between the two antenna arms is ~ 300
14 nm, as shown by the topography image acquired with the s-SNOM, and the extracted profiles of Fig. 5
15 a) and b), respectively. When the orientation of the incident polarization was along the main axis of
16 the antennas, the THz topography and the corresponding extracted profile, shown in Fig. 5 c) and d)
17 respectively, presented a strong E-field enhancement in the gap area. This is in very good agreement
18 with the simulation obtained for the normalized E-field by using Comsol Multiphysics software and
19 reported in the inset of Fig. 5 d). Conversely, when the polarization is perpendicular to the main axis
20 of the antenna, a weak THz signal is still observable at the boundary between the metallic antennas
21 and the dielectric, as shown in the SI, but no resonant enhancement of the E-field is observed in the
22 gap. It seems from the pictures acquired in Fig. 4 and Fig. 5 that the system is capable of retrieving
23 the enhancement of the E-field supported by resonant structures. Since the s-SNOM was operating in
24 tapping mode, it should be more sensitive to the vertical component of the E-field rather than to the in-
25 plane component. According to the simulation performed with Comsol multiphysics the two
26 components should have comparable strength. In the case on the resonant antenna of Fig. 5, we have
27 not observed a dipolar mode corresponding to the vertical component of the E-field, but this was
28 attributed to the limited resolution of the system. Operating the s-SNOM in shear-force mode rather
29 than tapping mode might help in determining which component is predominantly retrieved by this
30 system. Demodulation at higher harmonics, which is a common strategy to discriminate the
31 contribution arising from the polarized tip and the illuminated substrate, did not yield a significant
32 improvement in these experiments, but mainly reduced the total collected signal. This effect can be
33 attributed to the limited frequency response of the electronics implemented for demodulating the
34 signal, or to the self-mixing detection scheme itself, which is a strongly nonlinear process based on the
35 amount of scattered photons fed back into the laser cavity.

36 By further reducing all sources of noise, atmospheric perturbations, and placing the whole
37 apparatus in a nitrogen purged environment, the resolution is expected to improve to < 30 nm, a
38 level capable of investigating low-dimensional objects, such as quantum dots or nanowires [42]. The
39 main limits of the current system are represented by the non-optimal isolation from vibrations, and by
40 the environment perturbations. The first issue prevents the system from reaching its full capability in
41 resolution, while the latter is instead responsible for the unwanted fluctuations in the reflected THz
42 signal due to the strong water absorption in the laser path.

43 This home-made s-SNOM system has advantages over modified atomic force microscopes, in
44 terms of compactness and versatility, thus presenting the possibility of use at cryogenic
45 temperatures. This would facilitate completely new scenarios, allowing the active manipulation
46 of the quantum properties of low-dimensional quantum objects, such as nanowires and quantum dots
47 (QDs). We aim to locally excite QDs or quantum molecules, by selectively injecting THz photons in a
48 photon-assisted tunnelling experiment where transport is enabled by intraband absorption in the
49 confined hole states of QDs, or in the electronic band for molecules. A plethora of new experiments
50 can then be pursued aiming to perform spectroscopy of confined electron-hole systems. Finally, the
51 selective injection of single THz photons could be used to trigger the emission of a single near-
52 infrared photon from a QD, thus providing a THz-to-Telecom bridge in a quantum communication
53 system, and leading to the realization of an integrated quantum photon converter. In conclusion, we
54 have demonstrated a THz s-SNOM based on the self-mixing technique using QCLs. A 78 nm
55 resolution, corresponding to $> \lambda/1000$, was achieved with a QCL emitting around 2.85 THz. The
56 sensitivity of this approach has been further enhanced by partly suppressing lasing action and
57
58
59
60

1
2
3 simultaneously increasing the collection efficiency with an antireflection coated lens attached to a
4 laser facet. The system has been successfully implemented to retrieve the THz image of a photonic
5 crystal lattice of triangular holes and to map the plasmonic modes supported by planar antennas loaded
6 with graphene. This represents significant progress in the field of THz microscopy, and paves the way
7 to unique investigations of semiconductor quantum objects, bidimensional materials and biological
8 samples.
9

10 **Methods**

11
12 **QCL fabrication:** the QCL was fabricated with a single plasmon waveguide, with a bound-to-
13 continuum active region emitting around 2.85 THz. In order to enhance the sensitivity of the system,
14 as well as the collection of the scattered light, a silicon lens was attached to the QCL [43] with an 18.5
15 μm thick antireflection parylene coating. The lens mounting had two primary aims; increasing the
16 collection efficiency of the back-scattered light, and increasing the cavity mirror loss, rendering the
17 device more similar to a quantum cascade amplifier [44]. By carefully attaching the lens to the facet of
18 the laser using a layer of PMMA (polymethyl methacrylate), the emission was strongly reduced but
19 not fully suppressed. A partially suppressed laser emission is needed in order to align the beam onto
20 the metallic tip. The voltage-light-current characteristics of the device with and without feedback are
21 presented in the SI. The laser was operated at the current density corresponding to the maximum
22 emitted power. The optical path was finely adjusted in order to have a maximal back-scattered signal
23 into the cavity.
24

25 **Acquisition procedure:** the laser was mounted into the cryostat such that the E-field had a
26 polarization component along the tip shaft. The tuning fork with the metallic tip was mounted on a
27 printed circuit board connected with a piezoelectric motor stage arranged in the vertical z direction
28 with 65 μm travel range and 0.13 nm minimum step-size. When the system is brought into close
29 proximity to the sample surface, the tuning fork resonance is damped and the frequency, phase or Q-
30 factor can be used to close the feedback loop and keep a constant tip/sample distance, typically
31 between 30 nm and 100 nm. The sample is then scanned in the xy plane by using two piezoelectric
32 stages with 250 μm travel range in each direction and 0.4 nm minimum step size. For each xy position,
33 measurements were recorded for both the height of the tip, yielding the surface topography, and the
34 signal from the lock-in amplifier, corresponding to the THz scattered signal.
35

36 **Acknowledgements**

37 RDI, HEB, OM and DAR acknowledge financial support from the Engineering and Physical Sciences
38 Research Council (Grant No. EP/J017671/1, Coherent Terahertz Systems and Grant No.
39 EP/P021859/1 HyperTerahertz - High precision terahertz spectroscopy and microscopy). SH. and
40 PAB. acknowledge financial support from the Engineering and Physical Sciences Research Council
41 (Grant No. EP/K016636/1, GRAPHTED).
42

43 **Author Information**

44 Corresponding author. *Email: rd448@cam.ac.uk.
45 ORCID ID;
46 Riccardo Degl'Innocenti: 0000-0003-2655-1997
47

48 **Supporting Information Available**

49
50 Light-current-voltage characteristics of the QCL used in this work with and without the feedback.
51 Effective polarizability calculated for different substrates. Topography and corresponding THz image
52 of the antenna device shown in the main text but with the incident E-field polarization perpendicular to
53 the axis of the antenna. Relative profiles extracted from the topography and the THz image.
54

55 **Additional Data:** Additional data sets related to this publication are available from the Cambridge
56 University data repository at XXXX.


57 **References**

- 1
2
3 (1) Dhillon, S. S.; Vitiello, M. S.; Linfield, E. H.; Davies, A. G.; Hoffmann, M. C.; Booske, J.;
4 Paoloni, C.; Gensch, M.; Weightman, P.; Williams, G. P.; Castro-Camus, E.; Cumming, D. R. S.;
5 Simoens, F.; Escorcia-Carranza, I.; Grant, J.; Lucyszyn, S.; Kuwata-Gonokami, M.; Konishi, K.;
6 Koch, M.; Schmuttenmaer, C. A.; Cocker, T. L.; Huber, R.; Markelz, A. G.; Taylor, Z. D.;
7 Wallace, V. P.; Axel Zeitler, J.; Sibik, J.; Korter, T. M.; Ellison, B.; Rea, S.; Goldsmith, P.;
8 Cooper, K. B.; Appleby, R.; Pardo, D.; Huggard, P. G.; Krozer, V.; Shams, H.; Fice, M.; Renaud,
9 C.; Seeds, A.; Stöhr, A.; Naftaly, M.; Ridler, N.; Clarke, R.; Cunningham, J. E.; Johnston, M. B.
10 The 2017 terahertz science and technology roadmap *J. Phys. D: Appl. Phys.* **2017**, *50*, 043001.
- 11 (2) Lee, Y. S. Principles of Terahertz Science and Technology; Springer-Verlag USA, 2009.
- 12 (3) Cheon, H.; Yang, H.-J.; Lee, S.-H.; Kim, Y. A.; Son, J.-H. Terahertz molecular resonance of
13 cancer DNA. *Sci. Rep.* **2016**, *6*, 37103.
- 14 (4) Yazyev, O. V.; Chen, Y. P. Polycrystalline graphene and other two-dimensional materials. *Nat.*
15 *Nanotech.* **2014**, *9*, 755–767.
- 16 (5) Buron J. D.; Petersen, D. H.; Boeggild, P.; Cooke, D. G.; Hilke, M.; Sun, J.; Whiteway, E.;
17 Nielsen, P. F.; Hansen, O.; Yurgens, A.; Jepsen, P. U. Graphene Conductance Uniformity
18 Mapping. *Nano Lett.* **2012**, *12*, 5074–5081.
- 19 (6) Milot, R. L.; Sutton, R. J.; Eperon, G. E.; Haghighirad, A. A.; Hardigree, J. M.; Miranda, L.;
20 Snaith, H. J.; Johnston, M. B.; Herz, L. M. Charge-Carrier Dynamics in 2D Hybrid Metal–Halide
21 Perovskites. *Nano Lett.* **2016**, *16*, 7001–7007.
- 22 (7) Huber, A. J.; Keilmann, F.; Wittborn, J.; Aizpurua, J.; Hillenbrand, R. Terahertz Near-Field
23 Nanoscopy of Mobile Carriers in Single Semiconductor Nanodevices. *Nano Lett.* **2008**, *8*, 3766-
24 3770.
- 25 (8) Schnell, M.; Sarriurgarte, P.; Neuman, T.; Khanikaev, A. B.; Shvets, G.; Aizpurua, J.;
26 Hillenbrand, R. Real-Space Mapping of the Chiral Near-Field Distributions in Spiral Antennas and
27 Planar Metasurfaces. *Nano Lett.* **2016**, *16*, 663-670.
- 28 (9) Chen, J.; Badioli, M.; Alonso-Gonzalez, P.; Thongrattanasiri, S.; Huth, F.; Osmond, J.;
29 Spasenovic, M.; Centeno, A.; Pesquera, A.; Godignon, P.; Zurutuza Elorza, A.; Camara, N.;
30 Garcia de Abajo, F. J.; Hillenbrand, R.; Koppens, F. H. L. Optical nano-imaging of gate-tunable
31 graphene plasmons. *Nature* **2012**, *487*, 77-81.
- 32 (10) Nikitin, A. Y.; Alonso-Gonzalez, P.; Velez, S.; Mastel, S.; Centeno, A.; Pesquera, A.; Zurutuza,
33 A.; Casanova, F.; Hueso, L. E.; Koppens, F. H. L.; Hillenbrand, R. Real-space mapping of
34 tailored sheet and edge plasmons in graphene nanoresonators. *Nat. Photon.* **2016**, *10*, 239-244.
- 35 (11) Alonso-Gonzalez, P.; Nikitin, A. Y.; Gao, Y.; Woessner, A.; Lundeberg, M. B.; Principi, A.;
36 Forcellini, N.; Yan, W.; Velez, S.; Huber, A. J.; Watanabe, K.; Taniguchi, T.; Casanova, F.;
37 Hueso, L. E.; Polini, M.; Hone, J.; Koppens, F. H. L.; Hillenbrand, R. Acoustic terahertz graphene
38 plasmons revealed by photocurrent nanoscopy. *Nat. Nanotech.* **2017**, *12*, 31-35.
- 39 (12) Di Pietro, P.; Ortolani, M.; Limaj, O.; Di Gaspare, A.; Giliberti, V.; Giorgianni, F.; Brahlek, M.;
40 Bansali, N.; Koirala, N.; Oh, S.; Calvani, P.; Lupi, S. Observation of Dirac plasmons in a
41 topological insulator. *Nat. Nanotech.* **2013**, *8*, 556-560.
- 42 (13) Ju, L.; Geng, B.; Horng, J.; Girit, C.; Martin, M.; Hao, Z.; Bechtel, H. A.; Lian, X.; Zettl, A.; Ron
43 Shen, Y.; Wang, F. Graphene plasmonics for tunable terahertz metamaterials. *Nat. Nanotech.*
44 **2011**, *6*, 630-634.
- 45 (14) Vakil, A.; Engheta, N. Transformation Optics Using Graphene. *Science* **2011**, *332*, 1291-1294.
- 46 (15) Jadidi, M. M.; Sushkov, A. B.; Myers-Ward, R. L.; Boyd, A. K.; Daniels, K. M.; Gaskill, D. K.;
47 Fuhrer, M. S.; Drew, H. D.; Murphy, T. E. Tunable Terahertz Hybrid Metal–Graphene Plasmons.
48 *Nano Lett.* **2015**, *15*, 7099-7104.
- 49 (16) Jessop, D. S.; Kindness, S. J.; Xiao, L.; Braeuninger-Weimer, P.; Lin, H.; Ren, Y.; Ren, C. X.;
50 Hofmann, S.; Zeitler, J. A.; Beere, H. E.; Ritchie, D. A.; Degl'Innocenti, R. Graphene based
51 plasmonic terahertz amplitude modulator operating above 100 MHz. *Appl. Phys. Lett.* **2016**, *108*,
52 171101.
- 53 (17) Degl'Innocenti, R.; Jessop, D. S.; Sol, C. W. O.; Xiao, L.; Kindness, S. J.; Lin, H.; Zeitler, J. A.;
54 Braeuninger-Weimer, P.; Hofmann, S.; Ren, Y.; Kamboj, V. S.; Griffiths, J.; Beere, H. E.;
55 Ritchie, D. A. Fast Modulation of Terahertz Quantum Cascade Lasers Using Graphene Loaded
56 Plasmonic Antennas. *ACS Photon.* **2016**, *3*, 464-470.
57
58
59
60

- 1
2
3 (18) Chen, H.-T.; O'Hara, J. F.; Azad, A. K.; Taylor, A. J.; Averitt, R. D.; Shrekenhamer, D. B.;
4 Padilla, W. J. Experimental demonstration of frequency-agile terahertz metamaterials. *Nat.*
5 *Photon.* **2008**, *2*, 295-298.
- 6 (19) Zhou, J.; Chowdhury, D. R.; Zhao, R.; Azad, A. K.; Chen, H.-T.; Soukoulis, C. M.; Taylor, A. J.;
7 O'Hara, J. F. Terahertz chiral metamaterials with giant and dynamically tunable optical activity.
8 *Phys. Rev. B* **2012**, *86*, 035448.
- 9 (20) Cai, X.; Sushkov, A. B.; Suess, R. J.; Jadidi, M. M.; Jenkins, G. S.; Nyakiti, L. O.; Myers-Ward,
10 R. L.; Li, S.; Yan, J.; Gaskill, D. K.; Murphy, T. E.; Drew, H. D.; Fuhrer, M. S. Sensitive room-
11 temperature terahertz detection via the photothermoelectric effect in graphene. *Nat. Nanotech.*
12 **2014**, *9*, 814–819.
- 13 (21) Degl'Innocenti, R.; Xiao, L.; Kindness, S. J.; Kamboj, V.; Wei, B.; Braeuninger-Weimer, P.;
14 Nakanishi, K.; Aria, A.; Hofmann, S.; Beere, H. E.; Ritchie, D. A. Bolometric detection of
15 terahertz quantum cascade laser radiation with graphene-plasmonic antenna arrays. *J. Phys. D:*
16 *Appl. Phys.* **2017**, *50*, 174001.
- 17 (22) Degl'Innocenti, R.; Xiao, L.; Jessop, D. S.; Kindness, S. J.; Ren, Y.; Lin, H.; Zeitler, J. A.;
18 Alexander-Webber, J. A.; Joyce, H. J.; Braeuninger-Weimer, P.; Hofmann, S.; Beere, H. E.;
19 Ritchie, D. A. Fast Room-Temperature Detection of Terahertz Quantum Cascade Lasers with
20 Graphene-Loaded Bow-Tie Plasmonic Antenna Arrays. *ACS Photon.* **2016**, *3*, 1747–1753.
- 21 (23) Williams, B. Terahertz quantum-cascade lasers. *Nat. Photon.* **2007**, *1*, 517 – 525.
- 22 (24) Degl'Innocenti, R.; Montinaro, M.; Xu, J.; Piazza, V.; Pingue, P.; Tredicucci, A.; Beltram, F.;
23 Beere, H. E.; Ritchie, D. A. Differential near-field scanning optical microscopy with THz quantum
24 cascade laser sources. *Opt. Express* **2009**, *26*, 23785-23792.
- 25 (25) Mitrofanov, O.; Viti, L.; Dardanis, E.; Caterina Giordano, M.; Ercolani, D.; Politano, A.; Sorba,
26 L.; Vitiello, M. S. Near-field terahertz probes with room-temperature nanodetectors for
27 subwavelength resolution imaging. *Sci Rep.* **2017**, *7*, 44240.
- 28 (26) Dean, P.; Mitrofanov, O.; Keeley, J.; Kundu, I.; Li, L.; Linfield, E. H.; Davies, A. G. Apertureless
29 near-field terahertz imaging using the self-mixing effect in a quantum cascade laser. *Appl. Phys.*
30 *Lett.* **2016**, *108*, 091113.
- 31 (27) Dean, P.; Lim, Y. L.; Valavanis, A.; Kliese, R.; Nikolić, M.; Khanna, S. P.; Lachab, M.; Indjin,
32 D.; Ikonić, Z.; Harrison, P.; Rakić, A. D.; Linfield, E. H.; Davies, A. G. Terahertz imaging through
33 self-mixing in a quantum cascade laser. *Opt. Lett.* **2011**, *36*, 2587-2589.
- 34 (28) Valavanis, A.; Dean, P.; Lim, Y. L.; Alhathlool, R.; Nikolic, M.; Kliese, R.; Khanna, S. P.; Indjin,
35 D.; Wilson, S. J.; Rakic, A. D.; Linfield, E. H.; Davies, A. G. Self-Mixing Interferometry With
36 Terahertz Quantum Cascade Lasers. *IEEE Sensors J.* **2013**, *13*, 37-43.
- 37 (29) Ren, Y.; Wallis, R.; Jessop, D. S.; Degl'Innocenti, R.; Klimont, A.; Beere, H. E.; Ritchie, D. A.
38 Fast terahertz imaging using a quantum cascade amplifier. *Appl. Phys. Lett.* **2015**, *107*, 011107.
- 39 (30) Karrai, K.; Grober, R. Piezoelectric tip-sample distance control for near field optical
40 microscopes. *Appl. Phys. Lett.* **1995**, *66*, 1842- 1844.
- 41 (31) Ruitter, A. G.; Veerman, J. A.; Van Der Werf, K. O.; Van Hulst, N. F. Dynamic behavior of
42 tuning fork shear-force feedback. *Appl. Phys. Lett.* **1997**, *71*, 28-30.
- 43 (32) Atia, W. A.; Davis, C. C. A Phase-Locked Shear-Force Microscope for Distance Regulation in
44 Near-Field Optical Microscopy. *Appl. Phys. Lett.* **1997**, *70*, 405-407.
- 45 (33) Rychen, J.; Ihn, T.; Studerus, P.; Herrmann, A.; Ensslin, K. A low-temperature dynamic mode
46 scanning force microscope operating in high magnetic fields. *Rev. Sci. Instrum.* **1999**, *70*, 2765-
47 2768.
- 48 (34) Yang, C. H.; Chang, T. H.; Yang, M. J.; Moore, W. J. A low noise transimpedance amplifier for
49 cryogenically cooled quartz tuning fork force sensors. *Rev. Sci. Instrum.* **2002**, *73*, 2713-2716.
- 50 (35) Marshall, O. P.; Apostolopoulos, V.; Freeman, J. R.; Rungsawang, R.; Beere, H. E.; Ritchie, D.
51 A. Surface-emitting photonic crystal terahertz quantum cascade lasers. *Appl. Phys. Lett.* **2008**, *93*,
52 171112.
- 53 (36) Novotny, L.; Hecht, B. Principle of Nano-Optics; 3rd ed. Cambridge University Press,
54 Cambridge, UK, 2007.
- 55 (37) Knoll, B.; Keilmann, F. Near-field probing of vibrational absorption for chemical microscopy
56 *Nature* **1999**, *399*, 134-137.
57
58
59
60

- 1
2
3 (38) Knoll, B.; Keilmann, F. Enhanced dielectric contrast in scattering-type scanning near-field
4 microscopy. *Optics Commun.* **2000**, *182*, 321-328.
- 5 (39) Ordal, M. A.; Long, L. L.; Bell, R. J.; Bell, S. E.; Bell, R. R.; Alexander Jr, R. W.; Ward, C. A.
6 Optical properties of the metals Al, Co, Cu, Au, Fe, Pb, Ni, Pd, Pt, Ag, Ti, and W in the infrared
7 and far infrared. *Appl. Opt.* **1983**, *22*, 1099-1120.
- 8 (40) Ordal, M. A.; Bell, R. J.; Alexander, R. W.; Long, L. L.; Querry, M. R. Optical properties of
9 fourteen metals in the infrared and far infrared: Al, Co, Cu, Au, Fe, Pb, Mo, Ni, Pd, Pt, Ag, Ti, V,
10 and W. *Appl. Opt.* **1985**, *24*, 4493-4499.
- 11 (41) Ordal, M. A.; Bell, R. J.; Alexander, R. W.; Newquist, L. A.; Querry, M. R. Optical properties of
12 Al, Fe, Ti, Ta, W, and Mo at submillimeter wavelengths. *Appl. Opt.* **1988**, *27* 1203-1209.
- 13 (42) Eisele, M.; Cocker, T. L.; Huber, M. A.; Plankl, M.; Viti, L.; Ercolani, D.; Sorba, L.; Vitiello, M.
14 S.; Huber, R. Ultrafast multi-terahertz nano-spectroscopy with sub-cycle temporal resolution. *Nat.*
15 *Photon.* **2014**, *8*, 841-845.
- 16 (43) Degl'Innocenti, R.; Shah, Y. D.; Jessop, D. S.; Ren, Y.; Mitrofanov, O.; Beere, H. E.; Ritchie, D.
17 A. Hollow metallic waveguides integrated with terahertz quantum cascade lasers. *Opt. Express*
18 **2014**, *22*, 24439-24449.
- 19 (44) Ren, Y.; Wallis, R.; Shah, Y. D.; Jessop, D. S.; Degl'Innocenti, R.; Klimont, A.; Kamboj, V.;
20 Beere, H. E.; Ritchie, D. A. Single mode terahertz quantum cascade amplifier. *Appl. Phys. Lett.*
21 **2014**, *105*, 141102.
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

For Table of Contents Use Only

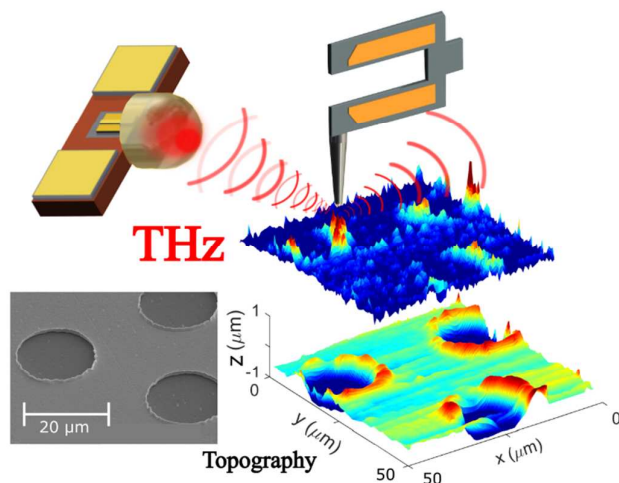

THz nanoscopy of plasmonic resonances with a quantum cascade laser

Riccardo Degl'Innocenti, Robert Wallis, Binbin Wei, Long Xiao, Stephen J. Kindness, Oleg Mitrofanov, Philipp Braeuninger-Weimer, Stephan Hofmann, Harvey E. Beere, David A. Ritchie

This article reports the realization of a near-field scattering optical microscope (s-SNOM) operating in the terahertz frequency range based on resonant quartz tuning forks and on quantum cascade lasers. The laser serves as both source and detecting element in a self-mixing scheme. The microscope achieved a spatial resolution of $> \lambda/1000$ at the emission frequency of ~ 2.85 THz. The s-SNOM system has been efficiently used to retrieve THz images with nm resolution of bi-dimensional photonic crystal arrays and resonant plasmonic antennas loaded with graphene, showing itself capable of mapping the electric field enhancement of the supported modes.

This article represents a significant step forward in the physics of sustainability, since it can be readily implemented for the investigation of a plethora of materials and their dielectric and plasmonic properties in the terahertz range with nm precision, and with a uniquely fast and sensitive detection scheme. Ultimately, this s-SNOM system represents a fundamental tool for the design and study of more efficient functional detectors and modulators based for example on novel materials, such as graphene or other 2D materials. Finally, once operating at cryogenic temperatures, the s-SNOM will have the potential to directly investigate and manipulate low dimensional quantum objects such as quantum dots. Accordingly, it can open new scenarios for the research of fundamental states of matter and of novel quantum circuitry.

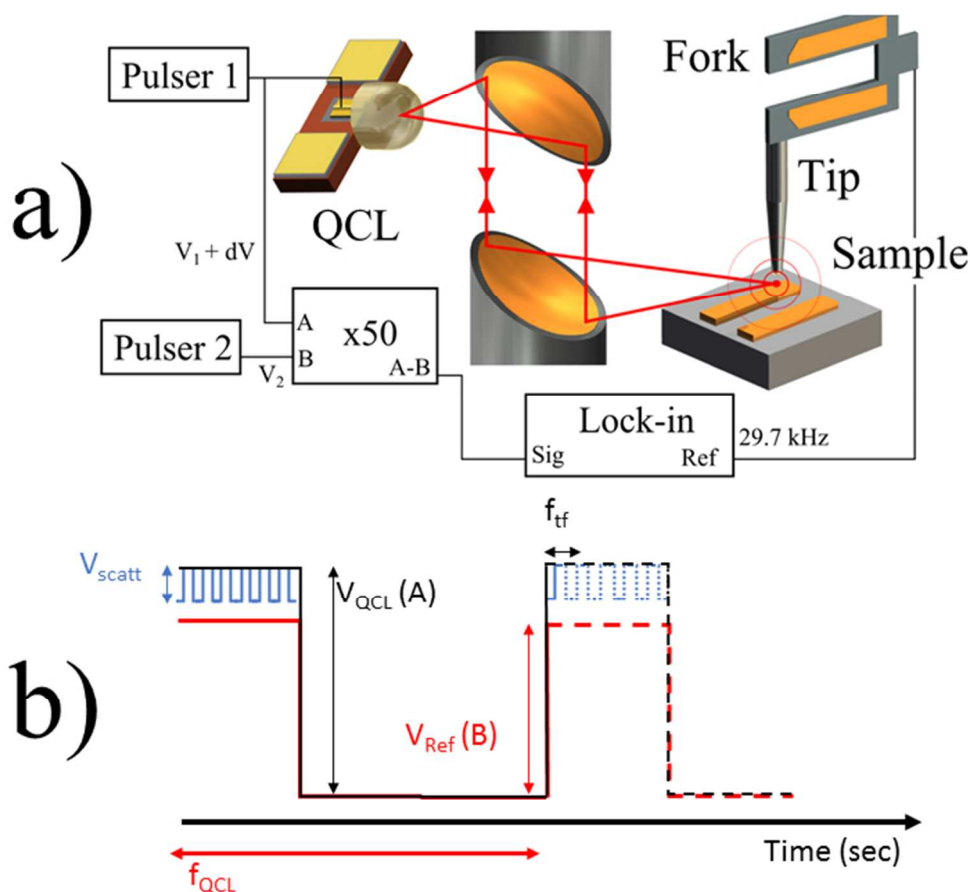


Figure 1. a) Schematic of the apparatus setup. The tuning fork oscillation frequency was set as the reference frequency of the lock-in amplifier. The tip/tuning fork system is arranged in order to operate in tapping mode. The input of the lock-in amplifier was given by the amplified voltage difference between the bias applied to the QCL and another, frequency synchronized, pulser. b) Acquisition scheme with the self-mixing technique. The scattered light into the cavity yields a reduction in the bias applied to the QCL V_{QCL} oscillating at the reference frequency of the tuning fork V_{tf} . This is compared to the bias of a second pulser V_{Ref} before being amplified.

191x173mm (96 x 96 DPI)

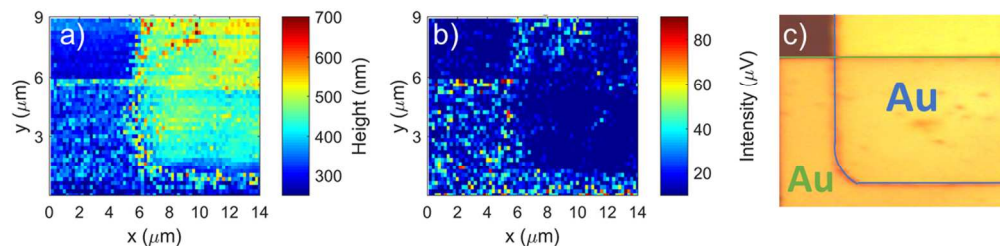


Figure 2. Topography a) and THz image b) of metallic features on SiO₂ substrate acquired with a step size of 200 nm. c) Optical micrograph of the region of interest showing the overlap between two metallic evaporations, over a SiO₂ substrate (top left corner). The metallic region defined with optical lithography (Ti/Au 10/500 nm) is reported in blue. The metallic area fabricated with electron beam lithography (Ti/Au, 80/20 nm) is indicated in green

336x82mm (96 x 96 DPI)

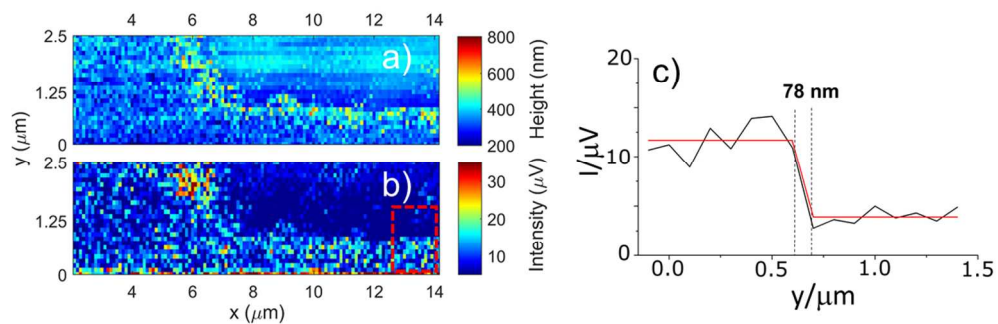


Figure 3. Topography a) and THz image b) acquired with 100 nm step-size of the metallic features shown in Fig. 2. From the profiles extracted in the dashed area in b) it was possible to obtain an estimation of the spatial resolution of the system c), calculated to be 78 nm, corresponding to $> \lambda/1000$.

333x107mm (96 x 96 DPI)

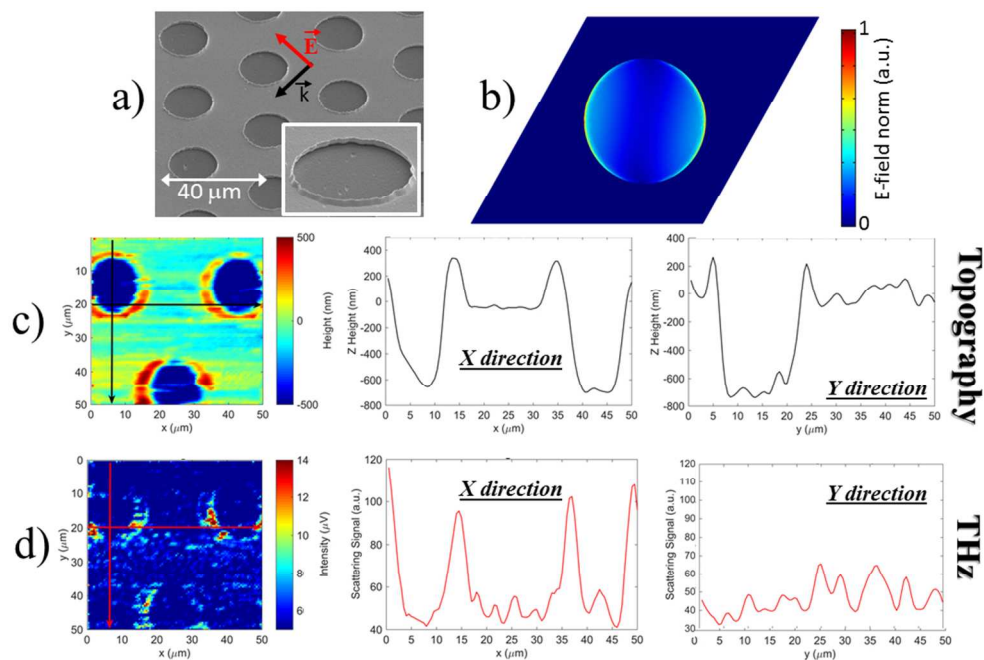


Figure 4. Near field microscopy of a SEPHC QCL emitting around 2.85 THz. a) SEM micrograph of the QCL top surface patterned with a triangular lattice of holes in a metallic surface for vertical emission. b) Normalized E-field at 2.8 THz simulated with Comsol Multiphysics for THz light incident as depicted in a). c) Topography and profiles extracted along the two acquisition directions d) THz scattered signal and the corresponding profiles extracted.

287x189mm (96 x 96 DPI)

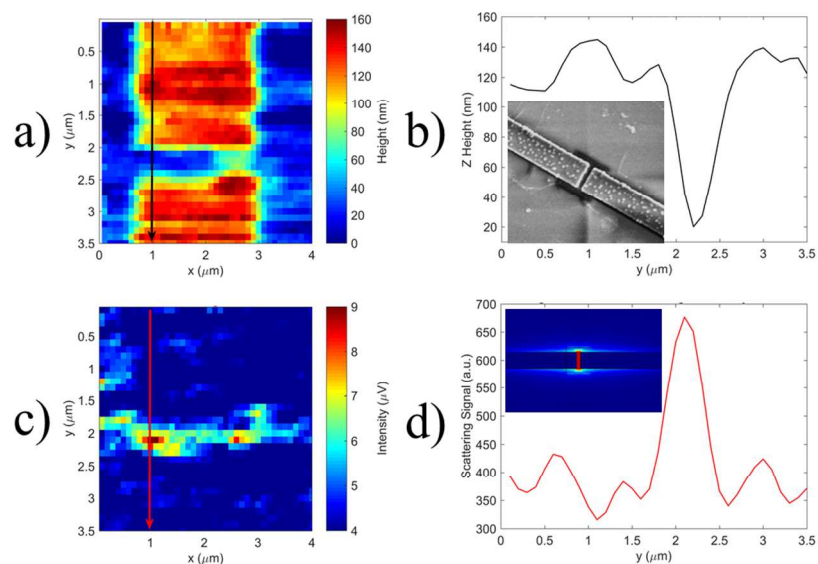


Figure 5. Plasmonic resonant antennas loaded with graphene illuminated with the E-field polarized along the major axis of the antennas. a) Topography of the resonant elements with ~ 300 nm gap. b) Relative extracted profile and SEM micrograph of the same element. c) THz signal and corresponding profile d) showing a strong E-field enhancement in the gap region, in very good agreement with the simulations obtained with the commercial software Comsol Multiphysics and reported in the inset.

338x190mm (96 x 96 DPI)