

Synthesis and Properties of a Compositional Series of MIL-53(AI) Metal-Organic Framework Crystal-Glass Composites

Christopher W Ashling, Duncan N. Johnstone, Remo N. Widmer, Jingwei Hou, Sean M. Collins, Adam F Sapnik, Alice M Bumstead, Philip A Chater, David A. Keen, and Thomas D. Bennett

J. Am. Chem. Soc., **Just Accepted Manuscript** • DOI: 10.1021/jacs.9b07557 • Publication Date (Web): 06 Sep 2019

Downloaded from pubs.acs.org on September 10, 2019

Just Accepted

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.

Synthesis and Properties of a Compositional Series of MIL-53(Al) Metal-Organic Framework Crystal-Glass Composites

Christopher W. Ashling¹, Duncan N. Johnstone¹, Remo N. Widmer², Jingwei Hou¹, Sean M. Collins¹, Adam F. Sapnik¹, Alice M. Bumstead¹, Paul A. Midgley¹, Philip A. Chater³, David A. Keen⁴, Thomas D. Bennett^{*}

¹. Department of Materials Science and Metallurgy, University of Cambridge, Cambridge, CB3 0FS, UK

². Department of Earth Sciences, University of Cambridge, Downing Street, Cambridge, CB2 3EQ, UK

³. Diamond Light Source Ltd, Diamond House, Harwell Campus, Didcot, Oxfordshire, OX11 0DE, UK

⁴. ISIS Facility, Rutherford Appleton Laboratory, Harwell Campus, Didcot, Oxfordshire, OX11 0QX, UK

ABSTRACT

Metal-organic framework crystal-glass composites (MOF-CGCs) are materials in which a crystalline MOF is dispersed within a MOF glass. In this work, we explore the room temperature stabilization of the open-pore form of MIL-53(Al), usually observed at high-temperature, which occurs upon encapsulation within a ZIF-62(Zn) MOF glass matrix. A series of MOF-CGCs containing different loadings of MIL-53(Al) were synthesized and characterized using X-ray diffraction and nuclear magnetic resonance spectroscopy. An upper limit of MIL-53(Al) that can be stabilized in the composite was determined for the first time. The nanostructure of the composites was probed using pair distribution function analysis and scanning transmission electron microscopy. Notably, the distribution and integrity of the crystalline component in a sample series was determined, and these findings related to the MOF-CGC gas adsorption capacity in order to identify the optimal loading necessary for maximum CO₂ sorption capacity.

INTRODUCTION

Metal-organic frameworks (MOFs) are hybrid, framework materials containing metal nodes that are linked in an extended fashion by organic molecules.¹ MOFs are highly regarded for their record breaking surface areas and tunable pore sizes^{2,3} and investigated for a plethora of applications including gas storage and separation, catalysis, water harvesting, and sensing.⁴⁻⁷ The exploitation of the full *chemical* promise of MOFs in practice may however be impeded by their *physical* form. Typically, MOFs are synthesized as microcrystalline powders of nm-mm sized particles that are ill-suited to industrial settings without prior processing.⁸ This has driven attempts to synthesize bulk materials (monoliths) using techniques such as sol-gel synthesis⁹⁻¹¹ or post-synthetic compaction and pelletization via, for example, spark-plasma sintering.^{12,13} Most MOF monolith research has however used a secondary material to aggregate the MOF crystallites such as in MOF-in-silica and mixed-matrix membrane systems.^{14,15}

Zeolitic imidazolate frameworks (ZIFs) are a sub-family of MOFs and have proven particularly suitable candidates for the synthesis of MOF monoliths. ZIFs are defined by their incorporation of imidazolate or imidazolate-based linkers, and are notable amongst MOFs for their high thermal stabilities (*ca.* 300–500°C).¹⁶⁻¹⁸ The incorporation of these bidentate linkers leads ZIFs to adopt many topologies identical to those of zeolites because the metal-imidazolate-metal dihedral angle is similar to that of silicon-oxygen-silicon (~145°).¹⁶ Several ZIFs have been observed to undergo

melting, forming extremely viscous MOF liquids at high temperatures, which can be quenched to form glasses.¹⁹ Structurally, the glass displays the same short-range order and stoichiometry of the crystalline material, *i.e.* the metal nodes retain a tetrahedral coordination with a connectivity that can be modelled as a continuous random network (CRN).²⁰

The glassy state of MOFs has been used to create MOF crystal-glass composites (MOF-CGCs), in which a crystalline phase is incorporated into a MOF-glass matrix.²¹ The first example of such a material was synthesized by forming a physical mixture of crystalline MIL-53(Al) [Al(OH)(bdc)] (bdc, 1,4-benzenedicarboxylate, C₈H₄O₄²⁻)—hereafter referred to as MIL-53—and ZIF-62(Zn) [Zn(Im)_{1.75}(blm)_{0.25}] (Im, imidazolate, C₃N₂H₃⁻; blm, benzimidazolate, C₇H₅N₂⁻)—hereafter referred to as ZIF-62.²¹ This mixture was heated above the melting temperature of ZIF-62, and cooled to room temperature to form the MOF-CGC (MIL-53)_{0.25}(a_gZIF-62)_{0.75}, (*i.e.* a MOF-CGC composed of 25 wt.% MIL-53 in a_gZIF-62, where a_g denotes the glassy form).

MIL-53 crystallizes in a “wine rack” structure (*Pnma*, *a* = 17.129(2) Å, *b* = 6.628(1) Å, *c* = 12.182(1) Å, $\alpha = \beta = \gamma = 90^\circ$) with large internal pores held open by excess solvent and unreacted ligand in the as-synthesized state (“MIL-53-as”).²² The removal or replacement of these guest molecules can cause the pore structure to undergo significant volume contraction or expansion, leading to phase transformations at different temperatures (Fig. 1a). When the pore occupying species are expelled, typically by heating, an open-pore structure (*Imma*, *a* = 6.608(1) Å, *b* = 16.675(3) Å, *c* = 12.813(2) Å, $\alpha = \beta = \gamma = 90^\circ$) is formed with a greater internal void

volume that we refer to as “MIL-53-lp” (large pore). The spontaneous uptake of water into the large-pore phase, typically upon cooling, causes the pores to contract to produce a narrow-pore structure (C_c, $a = 19.513(2)$ Å, $b = 7.612(1)$ Å, $c = 6.576(1)$ Å, $\alpha = \gamma = 90^\circ$, $\beta = 104.24(1)^\circ$) that we refer to as “MIL-53-np” (narrow pore).²² Reversible transitions between MIL-53-np and MIL-53-lp are known as “breathing”.

It was recently observed that when incorporated into a MOF-CGC, the MIL-53-lp structure was stabilized at room temperature (Fig. 1b) and because of the greater pore space compared to MIL-53-np, the (MIL-53)_{0.25}(a_gZIF-62)_{0.75} CGC displayed a CO₂ uptake greater than a combination of its parent materials.²¹ Motivated by this potential for composite formation to enhance gas sorption and to achieve designed stabilization of an open pore structure, we study here the maximum loading capacity of MIL-53 within a (MIL-53)_x(a_gZIF-62)_{1-x} series. Various characterization techniques are used to probe the chemical composition and structural integrity of the MOF-CGC components across the (MIL-53)_x(a_gZIF-62)_{1-x} series, and we pay particular attention to the MIL-53 phases present.

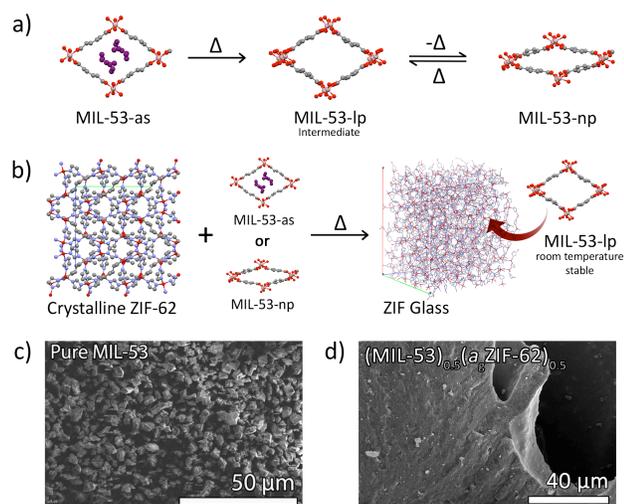


Figure 1. (a) Diagram of the activation process of MIL-53 and the transition between different states (C – grey, O – red, Al – pink, H – omitted for clarity, solvent – purple); (b) Schematic of composite formation using ball and stick figures of MIL-53, crystalline ZIF-62 (N – blue, Zn – red), and stick figure reverse Monte Carlo (RMC) model using combined X-ray and neutron total scattering data of a_gZIF-4 [Zn(Im)₂]¹⁹; (c) Scanning electron microscopy image (SEM) of MIL-53-as – from Hou *et al.*²¹ (d) Scanning electron microscope (SEM) image of (MIL-53)_{0.5}(a_gZIF-62)_{0.5}.

RESULTS AND DISCUSSION

Synthesis of MOF-CGC Series & Retention of MIL-53-lp

Samples of (MIL-53)_x(a_gZIF-62)_{1-x}, where $0.3 \leq x \leq 0.9$ in 0.1 increments, were synthesized by ball milling appropriate masses of crystalline ZIF-62 and MIL-53-as; pressing the resultant intimately-mixed powder in a 13 mm diameter dye at 0.74 GPa; heating to 450°C for 15 minutes; and quenching

to room temperature (see **Methods**). The materials produced were opaque, cream-colored monoliths, which became brown with increasing concentrations of MIL-53, ascribed to a small amount of thermal decomposition of the MIL-53 component. Neither parent material can be identified from SEM images and the relatively smooth surfaces of the bulk material provide evidence of appreciable flow in the ZIF-62 liquid state (Fig. 1c,d & S1-S5).

To verify that the stabilization of MIL-53-lp in (MIL-53)_x(a_gZIF-62)_{1-x} CGCs is not related to the presence of occluded ligand within MIL-53-as during CGC formation, a CGC was prepared using MIL-53-np as the starting material. The MIL-53-np was obtained by heating a sample of pure MIL-53-as to 330°C for 72 hours, to produce MIL-53-lp which was then cooled to room temperature and underwent the reported phase transition to MIL-53-np (Fig. 1, 2 & S6). A (MIL-53)_{0.25}(a_gZIF-62)_{0.75} CGC was then produced (see **Methods**) using this MIL-53-np starting material and was left in an unsealed container in ambient conditions for 24 hours before lab-source powder X-ray diffraction (PXRD) data was collected (See **Methods**). The experimental pattern displays agreement with the simulated pattern for MIL-53-lp and is dissimilar to MIL-53-np (Fig. 2). This demonstrates that the dominant MIL-53 phase present within (MIL-53)_{0.25}(a_gZIF-62)_{0.75} is MIL-53-lp regardless of the starting phase and further composite synthesis reported here were performed using MIL-53-as as the starting material.

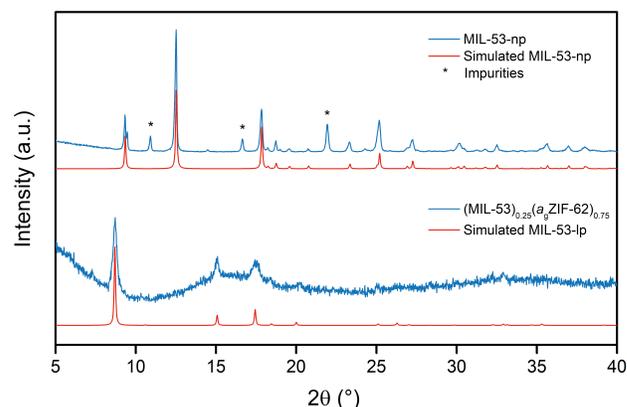


Figure 2. Experimental PXRD patterns (blue) of pure MIL-53-np (top) and the CGC (bottom). The simulated patterns (red) demonstrates the retention of the MIL-53-lp phase in quenched CGCs. Impurities marked with * have also been observed in prior literature.²³

Composition, MIL-53 Phase Identification, and Loading Capacity

The integrity and retention of organic linkers in MOF-CGCs across the composition series was studied using solution ¹H nuclear magnetic resonance (NMR) (see **Methods**). The presence of peaks assignable to HIm, HbIm and H₂bdc confirmed that the organic linkers present in crystalline ZIF-62 and MIL-53 were also present in all composites (Fig. 3a). A ratio of 1:6.93 between peak intensities corresponding to benzimidazole and imidazole respectively is observed, confirming that there was no change in ZIF-62 stoichiometry upon glass formation (Fig. 3b). The single expected signal arising from H₂bdc is

observed to increase, whilst those assigned to HIm and Hblm decrease, as the content of MIL-53 is increased across the MOF-CGC series (Fig. 3a).

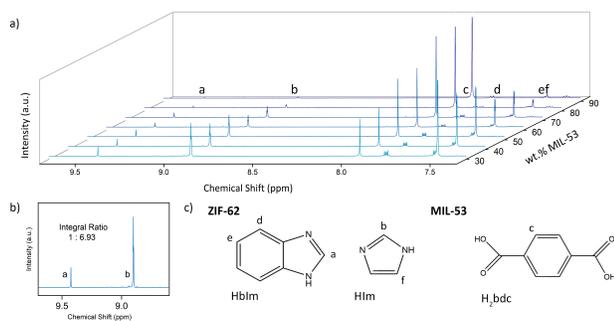


Figure 3. (a) ^1H NMR spectra of the $(\text{MIL-53})_x(\text{agZIF-62})_{1-x}$ MOF-CGC series using a 2.5:1 ratio of deuterated dimethyl sulfoxide and hydrochloric acid solvents, (b) Peak integral ratios of $(\text{MIL-53})_{0.25}(\text{agZIF-62})_{0.75}$, (c) Ligands within the frameworks. Peaks in the NMR spectra (a) are assigned (a-f) to protons in the ligands as indicated in (c).

Laboratory PXRD measurements ($\text{Cu } K_\alpha$ radiation, $\lambda = 1.5418 \text{ \AA}$) were carried out on the compositional series of finely ground $(\text{MIL-53})_x(\text{agZIF-62})_{1-x}$ samples (Fig. 4). The diffraction pattern for $(\text{MIL-53})_{0.3}(\text{agZIF-62})_{0.7}$ contained several peaks ascribed to the MIL-53-lp phase, of which the (101), (011), and (202) reflections were most prominent. No reflections were observed which could be ascribed to the MIL-53-np phase. However, upon increasing concentration of MIL-53 within the composite to 70 wt.%, peaks ascribed to the (200) and (110) reflections of MIL-53-np phase emerged and increased in relative intensity thereafter. Subsequently, room temperature X-ray total scattering data were collected for samples of the $(\text{MIL-53})_x(\text{agZIF-62})_{1-x}$ series (and the corresponding crystalline mixtures of the same proportions) using synchrotron radiation ($\lambda = 0.161669 \text{ \AA}$, see Methods). These data display a rise of a peak emerging at 1.3 \AA^{-1} for sample compositions of 70 wt.% MIL-53 and above (Fig. S7). This peak corresponds to the formation of the MIL-53-np phase and is in agreement with laboratory PXRD

Table 1. Crystallographic data determined from Rietveld analyses of total scattering data of the $(\text{MIL-53})_x(\text{agZIF-62})_{1-x}$ X-ray diffraction series. Rietveld refinement plots are shown in Figs S7-14.

| Sample | MIL-53-lp | | | | MIL-53-np | | | | |
|--|-----------|-----------|-----------|--------------|-----------|----------|----------|-------------|--------------|
| | a (Å) | b (Å) | c (Å) | Quantity (%) | a (Å) | b (Å) | c (Å) | β (°) | Quantity (%) |
| MIL-53-lp* | 6.608(1) | 16.675(3) | 12.813(2) | | | | | | |
| MIL-53-np* | | | | | 19.513(2) | 7.612(1) | 6.576(1) | 104.241(1) | |
| $(\text{MIL-53})_{0.3}(\text{agZIF-62})_{0.7}$ | 6.59(1) | 16.9(1) | 12.65(5) | 100 | | | | | 0 |
| $(\text{MIL-53})_{0.4}(\text{agZIF-62})_{0.6}$ | 6.61(2) | 16.7(2) | 12.71(9) | 100 | | | | | 0 |
| $(\text{MIL-53})_{0.5}(\text{agZIF-62})_{0.5}$ | 6.64(2) | 17.0(1) | 12.46(6) | 100 | | | | | 0 |
| $(\text{MIL-53})_{0.6}(\text{agZIF-62})_{0.4}$ | 6.64(2) | 17.0(1) | 12.44(4) | 100 | | | | | 0 |
| $(\text{MIL-53})_{0.7}(\text{agZIF-62})_{0.3}$ | 6.64(2) | 16.9(3) | 12.55(13) | 60(5) | 19.22(10) | 7.80(4) | 6.82(5) | 107.5(6) | 40(5) |
| $(\text{MIL-53})_{0.8}(\text{agZIF-62})_{0.2}$ | 6.63(2) | 16.8(3) | 12.63(11) | 55(5) | 19.37(11) | 7.73(3) | 6.91(4) | 106.2(4) | 45(5) |
| $(\text{MIL-53})_{0.9}(\text{agZIF-62})_{0.1}$ | 7.02(6) | 16.5(1) | 12.74(8) | 30(5) | 19.37(7) | 7.83(2) | 6.84(4) | 105.8(5) | 70(5) |

* Published data by Loiseau *et al.*²²

measurements. For greater phase determination accuracy, Rietveld refinement was performed on the synchrotron-source total scattering data using MIL-53-lp and MIL-53-np crystallographic information files (Table 1, Figs S7-14).²² The threshold for MIL-53-lp stabilization, using the materials processing described here, was therefore identified as between 60 and 70 wt.% MIL-53. Higher incorporations led to the emergence of MIL-53-np.

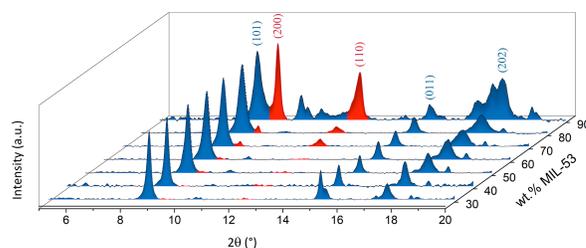


Figure 4. Laboratory powder X-ray diffraction patterns of the $(\text{MIL-53})_x(\text{agZIF-62})_{1-x}$ composite series, highlighting the MIL-53-np Bragg reflections in red. Background subtracted for clarity and normalized to the (101) peak of MIL-53-lp (blue).

Crystal-Glass Composite Microstructure

Scanning transmission electron microscopy (STEM) was used to investigate microstructure in the $(\text{MIL-53})_x(\text{agZIF-62})_{1-x}$ CGCs (Fig. 5). Scanning electron diffraction (SED) was used to map the number of Bragg diffraction peaks measured in the diffraction pattern recorded at each probe position, as the electron probe was scanned across the sample, to reveal the location of the crystalline phases in MOF-CGCs, as shown in Fig. 5c & Figs S15-17. These crystallinity maps demonstrate close contact between crystalline and non-crystalline regions within the MOF-CGCs across the composition range. Comparison with compositional maps showing the distribution of metal centers, obtained via STEM X-ray energy dispersive spectroscopy (STEM-EDS) mapping of the same particles and shown in Fig. 5a & Figs S15-17, confirms that the crystalline regions correspond to those which are rich in Al metal-centers, as expected for MIL-53.

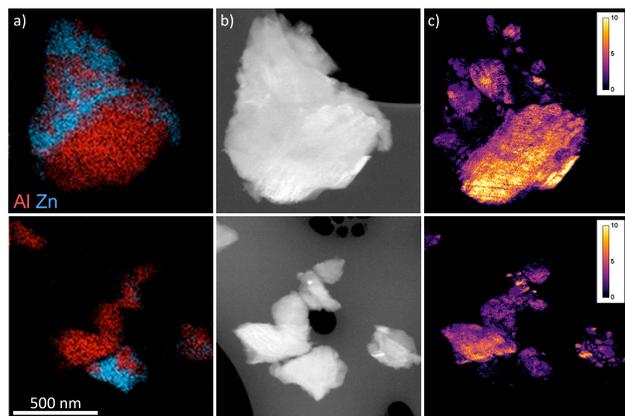


Figure 5. Scanning transmission electron microscopy of MOF-CGC particles from (MIL-53)_{0.6}(a_gZIF-62)_{0.4} (upper) and (MIL-53)_{0.9}(a_gZIF-62)_{0.1} (lower) samples. (a) Compositional maps of Al (red) and Zn (blue) metal centres from STEM-EDS mapping, (b) Annular dark-field images, and (c) Crystallinity maps showing the number of Bragg peaks as a function of probe position in SED data. The colour intensity scale for the crystallinity maps showing the number of Bragg scattering peaks identified at each probe position in the scanned field of view is presented for reference. Bragg peaks are only recorded from crystalline material and the number of peaks recorded at each position depends on the local crystal orientation. The scale is identical for all images.

Pair distribution function (PDF) analysis is emerging as a

powerful tool to investigate interatomic distances in crystalline and amorphous MOFs.^{24–26} This technique yields atom-atom correlation histograms, which effectively indicate distances within a sample and provide information on structure, regardless of crystallinity. Structure factors, $S(Q)$, were obtained from processing the total scattering data of both the (MIL-53)_x(a_gZIF-62)_{1-x} samples, and the corresponding crystalline mixtures, (MIL-53)(ZIF-62)(X/Y), where X and Y represent the respective weight percentages of each component. Those for the (MIL-53)(ZIF-62)(X/Y) series contain the Bragg scattering expected from both ZIF-62 and MIL-53, whereas structure factors from the (MIL-53)_x(a_gZIF-62)_{1-x} samples contain only that from MIL-53 (Figs S18–26). Appropriate corrections were performed with GudrunX software and the data were Fourier transformed to obtain the corresponding PDFs.²⁷

The intensity of the peaks in the PDFs of (MIL-53)(ZIF-62)(X/Y) vary proportionally between the two end members (MIL-53-as and crystalline ZIF-62) as a function of the relative proportions of each end member. This is unlike the PDFs of the (MIL-53)_x(a_gZIF-62)_{1-x} series which do not display the same ideal conformity between the end members of the series. This is likely due to (i) mixtures of MIL-53-np and MIL-53-lp phases, and (ii) possible interactions at the interfaces between the crystal and glass (Fig. 6). A comparison of the PDFs of (MIL-53)(ZIF-62)(X/Y) and (MIL-53)_x(a_gZIF-62)_{1-x} shows that correlations ascribed to the short-range order of ZIF-62 are retained after vitrification (Fig. 6a peaks 1–5). These peaks may be assigned to C-C (1.38 Å, 1), Zn-N (1.98 Å, 2), Zn-C (3.02 Å, 3), Zn-N (4.18 Å, 4), and Zn-Zn

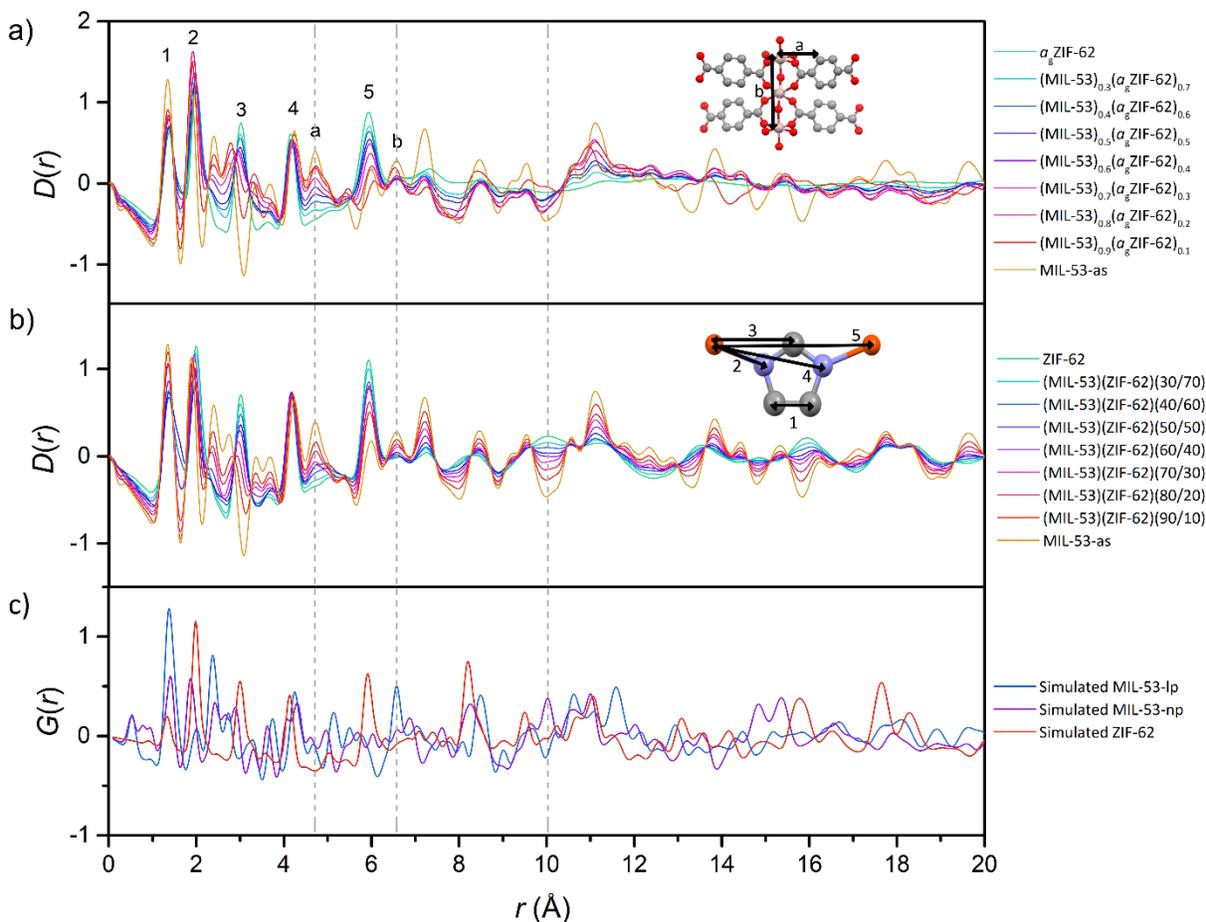


Figure 6. (a) Overlay PDF of the (MIL-53)_x(a_gZIF-62)_{1-x} series with a_gZIF-62 and MIL-53-as—MIL-53-as and MIL-53-lp are structurally similar and MIL-53-lp is unstable at room temperature. **Inset:** MIL-53-lp (Al – pink, O – red, C – grey) with correlation assignments (b) Overlay PDF of the (MIL-53)(ZIF-62)(X/Y) series with MIL-53 and ZIF-62. **Inset:** ZIF-62 (Zn – red, N – blue, C – grey) with correlation assignments, and (c) Simulated PDFs of MIL-53-lp, MIL-53-np and ZIF-62 using PDFGUI software.³⁷ Sub-1 Å data due to the way the solvent occupancies were modelled in

(5.96 Å, 5) interatomic distances. In the composites, correlations above 6 Å ascribed to ZIF-62 tend to zero due to the loss of long-range order. Interatomic distances associated with MIL-53 may be identified in both series (**Fig. 6a peaks a&b**)—these peaks are assigned to Al-C (4.71 Å, **a**), and Al-Al (6.57 Å, **b**) interatomic distances—though they are noticeably less intense due to weaker scattering of Al compared to Zn. In the composite series, all correlations past the short-range order of ZIF-62 (~8 Å) originate from crystalline MIL-53. Predicted PDF patterns for ZIF-62, MIL-53-as, MIL-53-np, and MIL-53-lp with their corresponding metal-metal and metal-(N or O) are provided in Supplementary Figures S27-30.

The PDF of (MIL-53)_{0.9}(a_gZIF-62)_{0.1} contains correlations at 10 and 14.5 Å, which qualitatively agree with peak positions in a predicted PDF for MIL-53-np (**Fig. S31**). These are absent in the experimental PDF of MIL-53-as. The identification of the MIL-53-np phase within the (MIL-53)_{0.9}(a_gZIF-62)_{0.1} agrees with PXRD data collected. We note that the PDFs of (MIL-53)_{0.8}(a_gZIF-62)_{0.2} and (MIL-53)_{0.7}(a_gZIF-62)_{0.3} do not display readily distinguishable MIL-53-np PDF correlations belonging to MIL-53-np. This may imply an insufficient concentration of the MIL-53-np phase is present in these samples to give rise to such correlations, especially considering that the peak at 10 Å corresponds to a minimum in the PDFs from MIL-53-lp and MIL-53-as.

Bulk Structure and Properties

A sample of (MIL-53)_{0.25}(a_gZIF-62)_{0.75} was previously observed to possess a CO₂ gas uptake of 66% that of a pure sample of MIL-53-np.²¹ Given that (i) MIL-53-lp is the main contributor to the adsorption capacity, and (ii) the phase of MIL-53 remains unaltered to loadings of ≤ 60 wt.%, the adsorption capacities are expected to increase across those composites displaying only the MIL-53-lp phase. Changes in adsorption trends are however expected on moving to compositions above 60 wt.%, *i.e.* the emergence of the MIL-53-np phase. The relationship between MIL-53 loading and gas uptake properties was probed using CO₂ gas adsorption isotherms for the full compositional series of MOF-CGCs (**Fig. 7**, for full isotherms see **Fig. S32**).

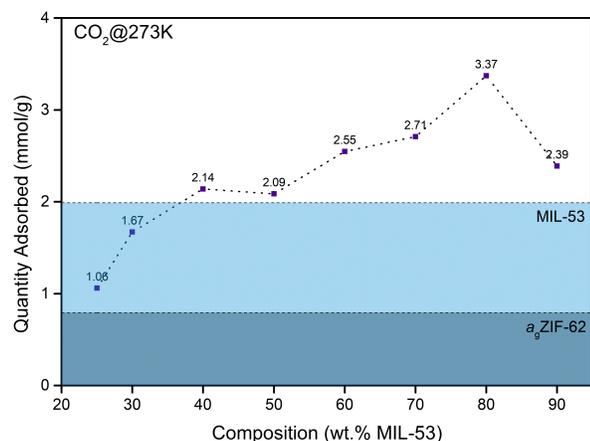


Figure 7. Quantity adsorbed from gas adsorption isotherms for (MIL-53)_x(a_gZIF-62)_{1-x} series at 1 bar pressure using CO₂

gas at 273 K. The quantities adsorbed for samples of activated MIL-53 (MIL-53-np, 1.99 mmol/g) and a_gZIF-62 (0.79 mmol/g) are displayed by light blue and dark blue areas respectively, from Hou *et al.*²¹.

For the samples of (MIL-53)_{0.25}(a_gZIF-62)_{0.75} - (MIL-53)_{0.6}(a_gZIF-62)_{0.4}, the total CO₂ quantity adsorbed increases in a broadly linear fashion, from 1.06 to 2.55 mmol/g, in accordance with the increasing concentration of MIL-53 in these samples, which is all present in the MIL-53-lp phase. A direct comparison of the gas sorption capacity of pure MIL-53-lp is not possible because the phase is unstable under the (room temperature) conditions used for gas adsorption measurement of these composites. Furthermore, any high temperature study on MIL-53-lp provides a poor comparison given the temperature dependence of gas adsorption.

(MIL-53)_{0.7}(a_gZIF-62)_{0.3} and (MIL-53)_{0.8}(a_gZIF-62)_{0.2} also display successively higher CO₂ adsorption. These two samples possess comparable amounts of MIL-53-lp, though the greater proportion of MIL-53 compared to a_gZIF-62 in the latter sample renders its total CO₂ uptake higher. A significant decline in capacity is observed for (MIL-53)_{0.9}(a_gZIF-62)_{0.1} as this material primarily comprises the MIL-53-np phase. Pure samples of MIL-53-np and a_gZIF-62 display CO₂ adsorption capacities of 1.99 and 0.79 mmol/g respectively (at 273 K at 1 bar pressure, **Fig. 7**). Furthermore, the sorption capacity of MIL-53-as is expected to be far lower than that of MIL-53-np due to the pore occupying species. Hence, compared with the room temperature stable forms of the pure MIL-53 (*i.e.* MIL-53-np and MIL-53-as), the composite has the greatest CO₂ capacity under ambient conditions. We also note that, as observed by Hou *et al.*,²¹ mesopores are expected in all of the composites, which will enhance CO₂ uptake capacity.

CONCLUSION

In this study we have synthesized a compositional series of (MIL-53)_x(a_gZIF-62)_{1-x} crystal-glass composites. Sample composition was confirmed by NMR which displayed relevant linker peak integrals varying in proportion to their relative contributions. The crystalline phase contribution of MIL-53 was determined by Rietveld refinement of X-ray diffraction studies—concluding that for MIL-53 loadings up to 60 wt.%, the only phase observed at room temperature is the metastable MIL-53-lp. Beyond this limit, a percentage of the excluded MIL-53-lp phase proceeds to form MIL-53-np upon cooling. This demonstrates a maximum total loading capacity of between 60-70 wt.% MIL-53 within a_gZIF-62 in this case. Gas adsorption measurements demonstrate that the maximum effective gas adsorption capacity of the (MIL-53)_x(a_gZIF-62)_{1-x} series is around 80 wt.%. Here, the MOF-CGC displays a CO₂ adsorption capacity 150% the value of pure MIL-53-np. A sample of just 30-40 wt.% loading of MIL-53 is expected to adsorb a similar quantity of CO₂ to a sample of pure MIL-53-np. These results show that relatively high loading capacities of crystalline MOFs within a MOF-glass can be achieved and provide a first look at the interesting physical properties which may arise as a result.

It is reasonable to propose that the encapsulation and stabilization of the metastable states of a range of breathing MOFs is possible, with the expected crystalline phase at room temperature in the composite being that which is stable at the quenching temperature of the matrix glass.

For the first time, the loading limit of a MOF-CGC system has been identified, opening multiple avenues for potential future research. One such avenue may be the advancement of processing methods, leading to larger incorporations of the active MOF component. Further studies of specific interest are as follows: (i) diffusion of various guest species into the composite material, (ii) predicting optimum loading limits, (iii) the effects of crystallite size, and (iv) attempts at shaping the bulk products formed. We believe that this may open routes to further functional MOF-CGCs and take advantage of many recent reports of MOF and coordination polymer glass formation.²⁸⁻³¹

METHODS

Synthesis of MIL-53(Al) Aluminum nitrate nonahydrate (26.00 g, 6.93×10^{-2} mol) and terephthalic acid (5.76 g, 4.96×10^{-2} mol) were dissolved in water (100 mL) and divided into 5 equal 20 mL aliquots over 5 Teflon-lined autoclaves. Each reaction vessel was placed in a 220°C preheated oven for 72 hours. The white crystalline product was washed with deionised water (3 x 30 mL) and dried overnight at 60°C.²²

Synthesis of ZIF-62 Zinc nitrate hexahydrate (3.30 g, 1.11×10^{-2} mol) and imidazole (17.82 g, 0.262 mol) were dissolved equally in *N,N*-dimethylformamide (150 mL) in two 250 mL screw top glass jars and stirred for 1 hour. Benzimidazole (3.10 g, 2.62×10^{-2} mol) was added to the solutions equally and was stirred for a further hour before closing the jars tightly and placing in an oven preheated to 130°C for 48 hours. The solutions were allowed to cool to room temperature before filtering and washing with DMF (3 x 30 mL) and DCM (1 x 30 mL) and placed in an oven at 60°C to dry overnight to yield a white crystalline powder (3.26 g), structure confirmed by PXRD.³²

Synthesis of (MIL-53)_x(a_gZIF-62)_{1-x} MOF-CGCs Crystalline ZIF-62 and MIL-53-as, were ball milled together using a Retsch MM 400 instrument, in appropriate wt. % ratios using a 7mm diameter stainless steel ball for 15 minutes, at a frequency of 30 Hz. The mixed powder was pressed in a 13 mm diameter die at 0.74 GPa for 1 minute. The pellet was then clamped between glass slides, heated to 450°C at a rate of 20°C/min, and held for 15 minutes, before being allowed to cool to room temperature under an Ar atmosphere.²¹

X-ray Powder Diffraction Data were collected on ground samples of the composite materials with a Bruker D8 Advance powder diffractometer using Cu K_{α} radiation ($\lambda = 1.5418 \text{ \AA}$) and a LynxEye position sensitive detector in Bragg-Brentano ($\theta - \theta$) parafocussing geometry at room temperature. Diffraction patterns were recorded at 2θ values of 5-40° with a time/step of 0.75 seconds over 1724 steps through a 0.012 mm Ni filter. PXRD patterns were analyzed by Rietveld refinements using TOPAS academic (V6) software.³³ Pseudo-Voigt peak shapes were globally refined as a single set of parameters for all scan files. A 9th-order Chebyshev polynomial background, a Gaussian background

peak accounting for the amorphous background from the ZIF-62 glass, scale factors, unit cell parameters of the MIL-53 structure, as well as 8th-order spherical harmonics preferred orientation corrections were refined individually for all scans.

Nuclear Magnetic Resonance NMR measurements were carried out by the NMR Service in The Department of Chemistry, University of Cambridge. Data were recorded on a Bruker 500 MHz DCH Cryoprobe Spectrometer. Samples were prepared for NMR by digesting each sample in 0.7 mL of a premixed solution of *d*⁶-dimethyl sulfoxide (3.5 mL) and deuterium chloride (1.4 mL), sonicating for 5 minutes and allowing 24 hours for the MOFs to dissolve.

¹H NMR spectra assignments: ¹H NMR (*d*⁶-DMSO, DCI, 500 MHz) δ_{H} 7.51 (d, CCHN, Imidazole, $J = 1.3$ Hz), 7.53 (dd, CCHC, Benzimidazole, $J = 6.2, 3.2$ Hz), 7.81 (dd, CCHC, Benzimidazole, $J = 6.2, 3.2$ Hz), 7.95 (s, Benzene-1,4-dicarboxylic acid, CCHC), 8.90 (t, NCHN, Imidazole, $J = 1.25$ Hz), 9.43 (s, NCHN, Benzimidazole)

Fourier Transformed Infra-Red Absorption Samples were finely ground and analysed using a Bruker Tensor 27, scanning wavenumbers of 1-2000 cm^{-1} over 10 scans (Fig. S33).

Analytical Scanning Transmission Electron Microscopy (STEM) was used to perform crystallinity mapping based on scanning electron diffraction (SED) and compositional mapping based on X-ray energy dispersive spectroscopy (EDS). Data was acquired using a JEOL ARM300F at the Diamond Light Source, UK fitted with a high-resolution pole piece, cold field emitter, and JEOL spherical aberration correctors in both the probe forming and image forming optics. The instrument was operated at 300 kV and aligned in an uncorrected nanobeam configuration and a 10-micron condenser aperture to obtain a convergence semi-angle of ~0.8 mrad and a diffraction limited probe diameter ~5 nm. Data was acquired with a scan step size of ~5.2 nm and a camera length of 20 cm. The probe current was ~2 pA. A Merlin-medipix direct electron detector,^{34,35} which is a counting type detector, was used to record the electron diffraction pattern at each probe position with an exposure time of 1 ms per probe position leading to a total electron fluence of ~5 $\text{e}/\text{\AA}^2$ based on the probe current, exposure time, and assuming a disk-like probe of the diameter above. SED was acquired over a raster pattern comprising 256x256 probe positions and each diffraction pattern comprised 256x256 pixels. X-ray energy dispersive spectroscopy (EDS) maps were acquired from the same regions, following SED acquisition, using a larger probe current, obtained using a 150 μm condenser aperture, in order to generate sufficient X-ray counts.

SED data were processed using the open source pyXem Python library to find diffraction peaks in every measured diffraction pattern using a difference of Gaussians method, which involves subtracting a blurred version of the diffraction pattern from a less blurred version of the diffraction pattern. EDS data were processed using the open-source HyperSpy Python library to produce maps for each X-ray emission line of interest (Al K_{α} , Zn K_{α}), which were extracted by integrating an energy window, background subtracted by linear interpolation from adjacent regions of the spectrum without other X-ray peaks present.

Pair Distribution Function Analysis Data were obtained at the I15-1 beamline, Diamond Light Source, UK ($\lambda = 0.161669 \text{ \AA}$, 72 KeV). All samples in both series of (MIL-53)_x(a_gZIF-62)_{1-x} and (MIL-53)(ZIF-62)(X/Y), along with pure samples of MIL-53-as, ZIF-62 and a_gZIF-62 and both crystalline and glass-ZIF-62 were finely ground before packing into sealed 1.17 mm (inner) diameter borosilicate capillaries. Data were taken of the background, empty capillary, and of all samples to a Q_{max} of 26 \AA^{-1} with a 10-minute acquisition time per sample. Normalized total scattering data were corrected individually using the GudrunX program to obtain the PDF of each sample.^{27,36} Predicted patterns were generated using crystallographic information files available online²² and the PDFGUI software.³⁷

Gas Adsorption CO₂ adsorption measurements were performed on a Micromeritics ASAP 2020 instrument at 273 K (in an ice water bath) using no less than 20 mg of sample. All samples were degassed at 90°C for 2 hours followed by 200°C for a further 2 hours prior to the adsorption/desorption tests (Fig. S34)

Scanning Electron Microscopy Data were collected on a high-resolution scanning electron microscope, FEI Nova NanoSEM 450. Shards of each monolithic MOF-CGC were coated in chromium prior to imaging.

ASSOCIATED CONTENT

Supporting Information

Scanning electron microscopy (SEM) images, PXRD, synchrotron X-ray total scattering data and corresponding Rietveld refinements, STEM images, structure factors ($S(Q)$), simulated PDF patterns, gas adsorption isotherms, IR, and BET surface areas are available in the supporting information.

Data Availability

All data generated in this study are included in this Article and the Supplementary Information and are also available from the corresponding authors upon request.

Code Availability

The code used to generate crystallinity maps (Johnstone, D. N. et al., pyXem 0.8.0, 2019) is available at <https://doi.org/10.5281/zenodo.2807711>. The code used to to produce maps for each X-ray emission line of interest (Peña, F. D. L. et al. hyperspy: HyperSpy 1.4.1, 2019) is available at <https://doi.org/10.5281/zenodo.1469364>.

AUTHOR INFORMATION

Corresponding Author

Please send any correspondence to tldb35@cam.ac.uk

Notes

The authors declare no competing financial interests.

ACKNOWLEDGMENTS

TDB would like to thank both the Royal Society for a University Research Fellowship (UF150021) and the Royal Society for

a Research Grant (RG94426). CWA would like to thank the Royal Society for a PhD studentship (RG160498), and the Commonwealth Scientific and Industrial Research Council for additional support (C2017/3108). Both JH and TDB gratefully acknowledge the EPSRC (EP/R015481/1). AFS acknowledges EPSRC for a studentship award under the Doctoral Training Programme. AMB acknowledges the Royal Society for funding (RGF\EA\180092), as well as the Cambridge Trust for a Vice Chancellor's Award (304253100). We extend our gratitude to Diamond Light Source, Rutherford Appleton Laboratory, UK, for access to Beamline I15-1 (EE20038-1) and access and support in the use of the electron Physical Science Imaging Centre (EM20195). SMC acknowledges the Henslow Research Fellowship at Girton College, Cambridge. PAM thanks the EPSRC for financial support under grant number EP/R025517/1.

REFERENCES

- (1) Furukawa, H.; Cordova, K. E.; O'Keeffe, M.; Yaghi, O. M. The Chemistry and Applications of Metal-Organic Frameworks. *Science* **2013**, *341* (6149), 1230444. <https://doi.org/10.1126/science.1230444>.
- (2) Hönickle, I. M.; Senkovska, I.; Bon, V.; Baburin, I. A.; Bönisch, N.; Raschke, S.; Evans, J. D.; Kaskel, S. Balancing Mechanical Stability and Ultrahigh Porosity in Crystalline Framework Materials. *Angew. Chemie - Int. Ed.* **2018**, *57* (42), 13780–13783. <https://doi.org/10.1002/anie.201808240>.
- (3) Farha, O. K.; Eryazici, I.; Jeong, N. C.; Hauser, B. G.; Wilmer, C. E.; Sarjeant, A. A.; Snurr, R. Q.; Nguyen, S. T.; Yazaydin, A. Ö.; Hupp, J. T. Metal-Organic Framework Materials with Ultrahigh Surface Areas: Is the Sky the Limit? *J. Am. Chem. Soc.* **2012**, *134* (36), 15016–15021. <https://doi.org/10.1021/ja3055639>.
- (4) Kim, H.; Yang, S.; Rao, S. R.; Narayanan, S.; Kapustin, E. A.; Furukawa, H.; Umans, A. S.; Yaghi, O. M.; Wang, E. N. Water Harvesting from Air with Metal-Organic Frameworks Powered by Natural Sunlight. *Science* **2017**, *356*, 430–434. <https://doi.org/10.1126/science.aam8743>.
- (5) Ma, S.; Zhou, H. C. Gas Storage in Porous Metal-Organic Frameworks for Clean Energy Applications. *Chem. Commun.* **2010**, *46* (1), 44–53. <https://doi.org/10.1039/b916295j>.
- (6) Li, J.-R.; Kuppler, R. J.; Zhou, H.-C. Selective Gas Adsorption and Separation in Metal-Organic Frameworks. *Chem. Soc. Rev.* **2009**, *38* (5), 1477–1504. <https://doi.org/10.1039/b802426j>.
- (7) Kreno, L. E.; Leong, K.; Farha, O. K.; Allendorf, M.; Van Duyne, R. P.; Hupp, J. T. Metal-Organic Framework Materials as Chemical Sensors. *Chem. Rev.* **2012**, *112* (2), 1105–1125. <https://doi.org/10.1021/cr200324t>.
- (8) Hindocha, S.; Poulston, S. Study of the Scale-up, Formulation, Ageing and Ammonia Adsorption Capacity of MIL-100(Fe), Cu-BTC and CPO-27(Ni) for Use in Respiratory Protection Filters. *Faraday Discuss.* **2017**, *201*, 113–125. <https://doi.org/10.1039/c7fd00090a>.
- (9) Tian, T.; Zeng, Z.; Vulpe, D.; Casco, M. E.; Divitini, G.; Midgley, P. A.; Silvestre-Albero, J.; Tan, J. C.; Moghadam, P. Z.; Fairen-Jimenez, D. A Sol-Gel Monolithic Metal-Organic Framework with Enhanced Methane Uptake. *Nat. Mater.* **2018**, *17* (2), 174–179. <https://doi.org/10.1038/NMAT5050>.
- (10) Sumida, K.; Liang, K.; Reboul, J.; Ibarra, I. A.; Furukawa, S.; Falcaro, P. Sol-Gel Processing of Metal-Organic Frameworks. *Chem. Mater.* **2017**, *29* (7), 2626–2645. <https://doi.org/10.1021/acs.chemmater.6b03934>.
- (11) Lohe, M. R.; Rose, M.; Kaskel, S. Metal-Organic Framework (MOF) Aerogels with High Micro- and Macroporosity.

- Chem. Commun.* **2009**, No. 40, 6056–6058. <https://doi.org/10.1039/b910175f>.
- (12) Widmer, R. N.; Lampronti, G. I.; Kunz, B.; Battaglia, C.; Shepherd, J. H.; Redfern, S. A. T.; Bennett, T. D. Manufacturing Macroporous Monoliths of Microporous Metal–Organic Frameworks. *ACS Appl. Nano Mater.* **2018**, *1* (2), 497–500. <https://doi.org/10.1021/acsanm.7b00335>.
- (13) Rubio-Martinez, M.; Avci-Camur, C.; Thornton, A. W.; Imaz, I.; Maspoch, D.; Hill, M. R. New Synthetic Routes towards MOF Production at Scale. *Chem. Soc. Rev.* **2017**, *46* (11), 3453–3480. <https://doi.org/10.1039/c7cs00109f>.
- (14) Zhu, Q.-L.; Xu, Q. Metal–Organic Framework Composites. *Chem. Soc. Rev.* **2014**, *43* (16), 5648–5512. <https://doi.org/10.1039/c3cs60472a>.
- (15) Denny Jr., M. S.; Moreton, J. C.; Benz, L.; Cohen, S. M. Metal–Organic Frameworks for Membrane-Based Separations. *Nat. Rev. Mater.* **2016**, *1*, 16078. <https://doi.org/10.1038/natrevmats.2016.78>.
- (16) Park, K. S.; Ni, Z.; Côté, A. P.; Choi, J. Y.; Huang, R.; Uribe-Romo, F. J.; Chae, H. K.; O’Keeffe, M.; Yaghi, O. M. Exceptional Chemical and Thermal Stability of Zeolitic Imidazolate Frameworks. *Proc. Natl. Acad. Sci. U. S. A.* **2006**, *103* (27), 10186–10191. <https://doi.org/10.1073/pnas.0602439103>.
- (17) Tian, Y. Q.; Zhao, Y. M.; Chen, Z. X.; Zhang, G. N.; Weng, L. H.; Zhao, D. Y. Design and Generation of Extended Zeolitic Metal–Organic Frameworks (ZMOFs): Synthesis and Crystal Structures of Zinc(II) Imidazolate Polymers with Zeolitic Topologies. *Chem. - A Eur. J.* **2007**, *13* (15), 4146–4154. <https://doi.org/10.1002/chem.200700181>.
- (18) Arhangelskis, M.; Katsenis, A. D.; Novendra, N.; Akimbekov, Z.; Gandrath, D.; Marrett, J. M.; Ayoub, G.; Morris, A. J.; Farha, O. K.; Frišćić, T.; Navrotsky, A. Theoretical Prediction and Experimental Evaluation of Topological Landscape and Thermodynamic Stability of a Fluorinated Zeolitic Imidazolate Framework. *Chem. Mater.* **2019**, *31*, 3777–3783. <https://doi.org/10.1021/acs.chemmater.9b00994>.
- (19) Gaillac, R.; Pullumbi, P.; Beyer, K. A.; Chapman, K. W.; Keen, D. A.; Bennett, T. D.; Coudert, F.-X. Liquid Metal–Organic Frameworks. *Nat. Mater.* **2017**, *16*, 1149–1155. <https://doi.org/10.1038/nmat4998>.
- (20) Bennett, T. D.; Yue, Y.; Li, P.; Qiao, A.; Tao, H.; Greaves, N. G.; Richards, T.; Lampronti, G. I.; Redfern, S. A. T.; Blanc, F.; Farha, O. K.; Hupp, J. T.; Cheetham, A. K.; Keen, D. A. Melt-Quenched Glasses of Metal–Organic Frameworks. *J. Am. Chem. Soc.* **2016**, *138* (10), 3484–3492. <https://doi.org/10.1021/jacs.5b13220>.
- (21) Hou, J.; Ashling, C. W.; Collins, S. M.; Krajnc, A.; Zhou, C.; Longley, L.; Johnstone, D. N.; Chater, P. A.; Li, S.; Coulet, M.-V.; Llewellyn, P. L.; Coudert, F.-X.; Keen, D. A.; Midgley, P. A.; Mali, G.; Chen, V.; Bennett, T. D. Metal–Organic Framework Crystal–Glass Composites. *Nat. Commun.* **2019**, *10* (1), 2580. <https://doi.org/10.1038/s41467-019-10470-z>.
- (22) Loiseau, T.; Serre, C.; Huguenard, C.; Fink, G.; Taulelle, F.; Henry, M.; Bataille, T.; Férey, G. A Rationale for the Large Breathing of the Porous Aluminum Terephthalate (MIL-53) Upon Hydration. *Chem. - A Eur. J.* **2004**, *10* (6), 1373–1382. <https://doi.org/10.1002/chem.200305413>.
- (23) Mounfield, W. P.; Walton, K. S. Effect of Synthesis Solvent on the Breathing Behavior of MIL-53(Al). *J. Colloid Interface Sci.* **2015**, *447*, 33–39. <https://doi.org/10.1016/j.jcis.2015.01.027>.
- (24) Bennett, T. D.; Goodwin, A. L.; Dove, M. T.; Keen, D. A.; Tucker, M. G.; Barney, E. R.; Soper, A. K.; Bithell, E. G.; Tan, J. C.; Cheetham, A. K. Structure and Properties of an Amorphous Metal–Organic Framework. *Phys. Rev. Lett.* **2010**, *104* (11), 2–5. <https://doi.org/10.1103/PhysRevLett.104.115503>.
- (25) Billinge, S. J. L.; Dykhne, T.; Juh, P.; Taylor, R.; Florence, J. Characterisation of Amorphous and Nanocrystalline Molecular Materials by Total Scattering. *CrystEngComm* **2010**, *12*, 1366–1368. <https://doi.org/10.1039/b915453a>.
- (26) Chapman, K. W.; Sava, D. F.; Halder, G. J.; Chupas, P. J.; Nenoff, T. M. Trapping Guests within a Nanoporous Metal–Organic Framework through Pressure-Induced Amorphization. *J. Am. Chem. Soc.* **2011**, *133* (46), 18583–18585. <https://doi.org/10.1021/ja2085096>.
- (27) Soper, A. K. *GudrunN and GudrunX: Programs for Correcting Raw Neutron and X-Ray Diffraction Data to Differential Scattering Cross Section*; Tech. Rep. RAL-TR-2011-2013 (Rutherford Appleton Laboratory Technical Report, Oxfordshire, **2011**).
- (28) Umeyama, D.; Horike, S.; Inukai, M.; Itakura, T.; Kitagawa, S. Reversible Solid-to-Liquid Phase Transition of Coordination Polymer Crystals. *J. Am. Chem. Soc.* **2015**, *137* (2), 864–870. <https://doi.org/10.1021/ja510191u>.
- (29) Kimata, H.; Mochida, T. Crystal Structures and Melting Behaviors of 2-D and 3-D Anionic Coordination Polymers Containing Organometallic Ionic Liquid Components. *Chem. - A Eur. J.* **2019**, *25*, 1–8. <https://doi.org/10.1002/chem.201900979>.
- (30) Zhao, Y.; Lee, S. Y.; Becknell, N.; Yaghi, O. M.; Angell, C. A. Nanoporous Transparent MOF Glasses with Accessible Internal Surface. *J. Am. Chem. Soc.* **2016**, *138* (34), 10818–10821. <https://doi.org/10.1021/jacs.6b07078>.
- (31) Frenzel-Beyme, L.; Kloß, M.; Pallach, R.; Salamon, S.; Moldenhauer, H.; Landers, J.; Wende, H.; Debus, J.; Henke, S. Porous Purple Glass-a Cobalt Imidazolate Glass with Accessible Porosity from a Meltable Cobalt Imidazolate Framework. *J. Mater. Chem. A* **2019**, *7* (3), 985–990. <https://doi.org/10.1039/c8ta08016j>.
- (32) Qiao, A.; Bennett, T. D.; Tao, H.; Krajnc, A.; Mali, G.; Doherty, C. M.; Thornton, A. W.; Mauro, J. C.; Greaves, G. N.; Yue, Y. A Metal–Organic Framework with Ultrahigh Glass-Forming Ability. *Sci. Adv.* **2018**, *4* (3), ea06827. <https://doi.org/10.1126/sciadv.a06827>.
- (33) Coelho, A. “*Topas Academia v6*” Coelho Software, Brisbane, Australia; 2007.
- (34) Nederlof, I.; Van Genderen, E.; Li, Y. W.; Abrahams, J. P. A Medipix Quantum Area Detector Allows Rotation Electron Diffraction Data Collection from Submicrometre Three-Dimensional Protein Crystals. *Acta Crystallogr. Sect. D Biol. Crystallogr.* **2013**, *69* (7), 1223–1230. <https://doi.org/10.1107/S0907444913009700>.
- (35) Mir, J. A.; Clough, R.; MacInnes, R.; Gough, C.; Plackett, R.; Shipsey, I.; Sawada, H.; MacLaren, I.; Ballabriga, R.; Maneuski, D.; O’Shea, V.; McGrouther, D.; Kirkland, A. I. Characterisation of the Medipix3 Detector for 60 and 80 KeV Electrons. *Ultramicroscopy* **2017**, *182*, 44–53. <https://doi.org/10.1016/j.ultramic.2017.06.010>.
- (36) Soper, A. K.; Barney, E. R. Extracting the Pair Distribution Function from White-Beam X-Ray Total Scattering Data. *J. Appl. Crystallogr.* **2011**, *44* (4), 714–726. <https://doi.org/10.1107/s0021889811021455>.
- (37) Farrow, C. L.; Juhas, P.; Liu, J. W.; Bryndin, D.; Boin, E. S.; Bloch, J.; Proffen, T.; Billinge, S. J. L. PDFfit2 and PDFgui: Computer Programs for Studying Nanostructure in Crystals. *J. Phys. Condens. Matter* **2007**, *19* (33), 1–7. <https://doi.org/10.1088/0953-8984/19/33/335219>.

TOC FIGURE:

